

Three-phase plane composites of minimal elastic stress energy: High-porosity structures

Andrej Cherkaev^{a,*}, Grzegorz Dzierżanowski^b

^a*Department of Mathematics, University of Utah, Salt Lake City, UT, USA.*

^b*Faculty of Civil Engineering, Warsaw University of Technology, Warsaw, Poland.*

Abstract

The paper establishes tight lower bound for effective elastic stress energy of two-dimensional three-phase anisotropic composites. It is assumed that the materials are mixed with fixed volume fractions and that one of the phases is degenerated to void, i.e. the effective material is porous. The bound expands the Hashin–Shtrikman and translation bounds to multiphase structures. It is derived using a combination of the translation method and additional inequalities on the stress fields in materials; similar technique was used by Cherkaev (Mech. Mater. 41, 411-433, 2009) for isotropic multiphase composites. It is shown that in the high-porosity regime the obtained energy estimate is exact and it is realized on microstructures in the form of high-rank laminates whose optimal geometrical parameters are explicitly found. To this end, the field matching method is elaborated for the plane elasticity problem, following Albin et al. (J. Mech. Phys. Solids 55, 1513-1553, 2007) and Cherkaev and Zhang (Int. J. Solids Struct. 48, 2800-2813, 2011) where similar technique was developed for conductivity case. Corresponding formulae solving the “G-closure problem” of a three-phase composite are also derived. Conjectures regarding low-porosity regimes are presented. However, full discussion of this issue is postponed to a separate publication.

Keywords: Multimaterial composites, Minimal stress energy, Bounds for effective properties, Optimal microstructures, High-rank laminates

*Corresponding author. Address: Department of Mathematics, 155S 1400E, University of Utah, Salt Lake City, UT 84112, USA. Tel: +1 801 581 6822/6851; fax: +1 801 581 4181.

Email addresses: `cherk@math.utah.edu` (Andrej Cherkaev), `gd@il.pw.edu.pl` (Grzegorz Dzierżanowski)

1. Introduction

Significance of the problem Optimization of composite microstructures is important today because technological capabilities allow for manufacturing a huge variety of microscopic designs for roughly the same price, and one wants to know what “the best” microstructure is. There is no boundary between *optimal structural design* in classical engineering sense and *optimal composite material* as the latter is also a structure at microlevel. Optimal large-scale structures are made from optimal microstructures (composites) and the main difference between them is that the composite problem is solved for a periodic domain and periodic boundary conditions, which permits for an explicit solution. Besides the optimal structures, one wants to know the range of the improvement of overall composite properties by varying the microstructure - the quasiconvex envelope problem, see for example (Cherkaev, 2000; Dacorogna, 2008) - which opens ways to construction of metamaterials, i.e. structures with unusual responses.

So far, the vast majority of available results deals with two-material composites. Meanwhile, numerous applications call for optimal design of multi-material composites, or even porous composites from two elastic materials and void, especially applications that utilize multi-physics, i.e. elastic and electromagnetic properties and those that deal with structures best adapted to variable environment such as natural morphologies perfected by evolution.

Optimal microstructures of two-phase and multiphase composites are drastically different. In contrast with the steady and intuitively expected topology of two-material optimal mixture (a strong material always surrounds weak inclusions), optimal multimaterial structures show the large variety of patterns and the optimal topology depends on volume fractions. Optimal multiphase structure may contain an enveloping layer but it also has “hubs” of a material with intermediate stiffness connected by “pathways” (laminate of the best and worst materials) and other configurations that reveal a geometrical essence of optimality, see (Cherkaev, 2009; Cherkaev and Zhang, 2011; Cherkaev, 2012) and Figure 1. Geometries of multimaterial optimal structures are not unique, pieces of the same material may occur in different places of an optimal structure and they may correspond to different fields inside them. Clearly, the method for finding optimal multiphase geometries differ from those for optimal two-material structures.

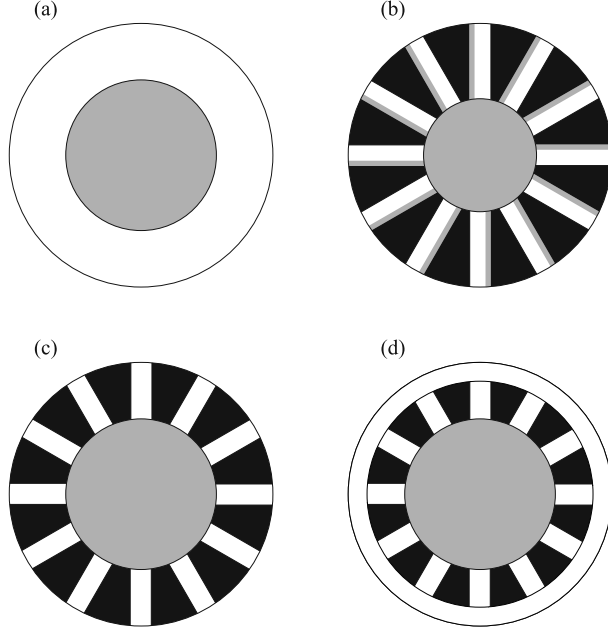


Figure 1: Composites made from two isotropic materials and void (white and grey colors represent stronger and weaker phases respectively, black corresponds to void). Comparison of geometries of optimal microstructures with maximal effective bulk modulus: (a) two-material composite; (b)-(d) three-material microstructures with small, intermediate and large volume of stronger material. The amount of weaker material is kept constant in all cases.

In this paper, we follow (Cherkaev and Zhang, 2011) in developing the technique for finding the bounds and optimal structures and we apply it to determining optimal elastic composites. The results constitute a next step from the popular “topology optimization”, see (Bendsøe and Sigmund, 2003), that is a problem of optimal layout of a material and void. Namely, we describe an optimal distribution of two materials and void, or an optimal two-material porous composite made from an expensive and strong material, a weak and cheap one, and void. Such problem is useful for many multi-physics design applications when additional properties besides elasticity are important. For example, the presence of one of the materials can be independently required by the reasons different from an optimal elastic response. The above-mentioned consideration puts forward new challenges, such as approximation of complex optimal structures with simpler ones, selection of the

cases where three and more materials should be mixed in the same spot, etc.

Background of the research Formally, the problem of optimal structures can be formulated as a question of minimizers of a variational problem with nonquasiconvex multiwell Lagrangians; the wells represent components' energies plus their costs and the minimizers (Young measures) are stress fields in the materials of an optimal composite. The challenging open problem is to build the quasiconvex envelope for Lagrangian with three or more wells. The problem is addressed by (i) finding exact bound (the lower bound for the quasiconvex envelope) and (ii) approximating these bounds by special class of minimizers. By building the lower bound, we also obtain sufficient conditions on optimal fields in materials that hint on the search for geometric patterns determining optimal structures, see (Milton, 2002; Albin et al., 2007; Cherkaev, 2009).

The existing techniques for the bound such as Hashin-Shtrikman method, see (Hashin and Shtrikman, 1963); translation method, see (Lurie and Cherkaev, 1982; Lurie and Cherkaev, 1986; Tartar, 1985; Milton, 2002) or analytic method of Bergman-Milton, see (Bergman, 1978; Milton, 1981a, 2002), produced a number of results for two-material mixtures in the last 25 years, see e.g. the books (Lurie, 1993; Cherkaev, 2000; Allaire, 2002; Milton, 2002; Dacorogna, 2008) for examples. These techniques, however, do not provide exact solutions for multiwell problems. This, in turn, poses a mathematical challenge that needs to be addressed.

In the last three decades, the multimaterial optimal composites have been studied by Milton (Milton, 1981b), Lurie & Cherkaev (Lurie and Cherkaev, 1985), Milton & Kohn (Milton and Kohn, 1988), Gibiansky & Sigmund (Gibiansky and Sigmund, 2000) among others. In 1995, Nesi published a paper (Nesi, 1995) about bounds for multimaterial mixtures that are better than Hashin-Shtrikman ones.

In the last years (2009-2012), a new technique was suggested (Cherkaev, 2009; Cherkaev and Zhang, 2011; Cherkaev, 2012) for finding optimal bounds for multimaterial mixtures and tested at a couple of examples. The essence of the new technique is coupling the translation method with the Alessandrini-Nesi inequality, see (Alessandrini and Nesi, 2001), that order and restrain values of the fields in any optimal composite. Roughly speaking, in the case tackled in this paper (elastic 2D microstructures of maximal stiffness for a mixture of two materials and void), it states that the sign of a stress

field is constant in the whole microstructure. The technique was used to find the bounds of isotropic 2D multimaterial composites, see (Cherkaev, 2009, 2012); anisotropic conducting composites made from two materials and void, see (Cherkaev and Zhang, 2011). In all these cases, as well as in the present research, the lower bound is a multifaceted surface. Its analytic expression varies depending on the convexity of the wells. In these problems, the structure of optimal fields in each material of the composite is analyzed and described for all cases but one, where the bound and the conjuncted optimal microstructures are still slightly different, see the discussion in (Cherkaev and Zhang, 2011). Our guess is that there is another, yet unaccounted, inequality which becomes active in the latter case.

2. Problem setting

2.1. Notation

Reference to periodic homogenization. Consider a domain $\Omega \subset \mathbb{R}^2$ filled with two linearly elastic materials and a void. Non-homogeneous distribution of phases in the domain is determined by its division into three disjoint subsets Ω_i , $i = 1, 2, 3$. Suppose that a boundary value problem (BVP) of linearized elasticity is posed in Ω . If non-homogeneity of material layout is given by a fine partition of the domain then a solution to the BVP may be difficult to obtain even numerically. In such case, it is convenient to make use of the homogenization theory of periodic media in determining the simplified, effective Hooke's law in Ω prior to solving the BVP.

The homogenization theory defines effective elastic moduli of a given periodic structure, see e.g. (Cherkaev, 2000; Tartar, 2000) for the most recent exposition of the topic. In this paper, we solve an inverse homogenization problem: we find a structure of a multicomponent composite that stores minimal stress energy in a given homogeneous stress field. We assume that the properties of constituent materials and their volume fractions $m_i \in [0, 1]$, $i = 1, 2, 3$, $m_1 + m_2 + m_3 = 1$, are given.

Definitions. Due to local character of homogenization, in the sequel we consider arbitrary $x \in \Omega$ which is sufficiently distant from the boundary $\partial\Omega$. Let $Y = [0, 1]^2$ denote a corresponding unit cell periodically extended to $\mathbb{R}^2$. Assume that Y is divided into three disjoint subcells Y_i , $i = 1, 2, 3$,

whose areas m_i are fixed. Write

$$Y = \bigcup_{i=1,2,3} Y_i, \quad |Y_i| = m_i, \quad \sum_{i=1}^3 m_i = 1 \quad (1)$$

and set (e_1, e_2) for a Cartesian basis in Y . Let $\mathbb{E}_s^2$ stand for a space of plane, second-order symmetric tensors, and $\mathbb{E}_s^4$ for the space of plane Hooke's tensors. Next, choose

$$\begin{aligned} E_1 &= \frac{1}{\sqrt{2}}(e_1 \otimes e_1 + e_2 \otimes e_2), \quad E_2 = \frac{1}{\sqrt{2}}(e_1 \otimes e_1 - e_2 \otimes e_2), \\ E_3 &= \frac{1}{\sqrt{2}}(e_1 \otimes e_2 + e_2 \otimes e_1) \end{aligned} \quad (2)$$

for the basis in $\mathbb{E}_s^2$.

Suppose that Y_1 and Y_2 are filled with elastic isotropic materials whose constitutive properties are given by $K_i = 1/k_i$, $L_i = 1/\mu_i$, $i = 1, 2$, where k_i and μ_i stand for bulk and shear moduli of i -th phase. Let $K_3 = L_3 = +\infty$ which means that the third phase corresponds to void. Introduce a set $A = \{A_1, A_2, A_{\text{void}}\}$ where

$$A_i = \frac{K_i}{2} E_1 \otimes E_1 + \frac{L_i}{2} (E_2 \otimes E_2 + E_3 \otimes E_3) \quad (3)$$

represents Hooke's compliance tensor of i -th non-degenerate isotropic phase. In the sequel we assume that the materials are well-ordered, i.e. $K_1 < K_2 < K_3 = +\infty$ and $L_1 < L_2 < L_3 = +\infty$.

Set

$$\tau_0 = 1 e_1 \otimes e_1 + \varrho e_2 \otimes e_2$$

for the average stress tensor in Y . Components 1 and ϱ denote principal values of τ_0 and (e_1, e_2) stands for its principal basis. It follows that

$$\tau_0 = S_0 E_1 + D_0 E_2, \quad S_0 = \frac{1 + \varrho}{\sqrt{2}}, \quad D_0 = \frac{1 - \varrho}{\sqrt{2}}$$

and S_0, D_0 represent spherical and deviatoric components of τ_0 . Without loss of generality we may assume $|\varrho| \leq 1$. It is understood that τ_0 denotes a value (calculated at $x \in \Omega$) of a stress field solving the homogenized BVP.

Next, define a set of stress fields statically admissible in Y

$$\Sigma = \left\{ \tau : \tau \in L^2_{\#}(Y, \mathbb{E}_s^2), \operatorname{div} \tau = 0 \text{ in } Y, \int_Y \tau(y) dy = \tau_0 \right\}$$

where $L^2_{\#}(Y, \mathbb{E}_s^2)$ stands for the space of L^2 -functions with values in $\mathbb{E}_s^2$ and Y -periodic in Ω . Fields $\tau = \tau(y)$ belonging to this space are thus uniquely represented in (2) by one spherical and two deviatoric components, respectively given by $s = s(y)$ and $d_1 = d_1(y)$, $d_2 = d_2(y)$, such that

$$s = \frac{\tau_{11} + \tau_{22}}{\sqrt{2}}, \quad d_1 = \frac{\tau_{11} - \tau_{22}}{\sqrt{2}}, \quad d_2 = \sqrt{2} \tau_{12}$$

hence $\tau(y) = s(y) E_1 + d_1(y) E_2 + d_2(y) E_3$.

Due to Y -periodicity, $\tau \in \Sigma$ is endowed with two properties:

- function $\det \tau(y)$, $y \in Y$, is quasilinear hence

$$\int_Y \det \tau(y) dy = \det \tau_0 = \varrho; \tag{4}$$

- function $\det \tau(y)$, $y \in Y$, is locally univalent with $\det \tau_0$, that is

$$\det \tau(y) \geq 0 \text{ a.e. in } Y \text{ if } \det \tau_0 = \varrho \geq 0 \tag{5}$$

and the latter remains valid if “ $\geq$ ” is replaced by “ $\leq$ ”,

see (Alessandrini and Nesi, 2001). The above-mentioned properties do not result in any restrictions on $\tau \in \Sigma$, they simply unveil certain characteristics of the stress fields related to assumed Y -periodicity. Nevertheless, (4) and (5) are of great significance in bounding the stress energy which is the central part of the study.

Decomposing the determinant function of a stress field according to

$$2 \det \tau = s^2 - (d_1^2 + d_2^2)$$

and considering $\varrho \in [-1, 1]$, allows for rewriting (5) in the form

$$\begin{aligned} s^2(y) &\geq d_1^2(y) + d_2^2(y) \text{ a.e. in } Y \text{ if } \varrho \in [0, 1], \\ s^2(y) &\leq d_1^2(y) + d_2^2(y) \text{ a.e. in } Y \text{ if } \varrho \in [-1, 0]. \end{aligned} \tag{6}$$

For further considerations, let us rephrase the requirements imposed on $\tau \in \Sigma$. First, define a set

$$\Sigma_{\text{uni}} = \left\{ \tau : \tau \in L_{\#}^2(Y, \mathbb{E}_s^2) \text{ with univalence property as in (6), } \right\}.$$

Next, write the restriction on the mean stress ($\int_Y \tau = \tau_0$) in a form

$$\Sigma_{\text{av}} = \left\{ \begin{array}{ll} S_i, D_{ij}, \quad i, j = 1, 2: & m_1 S_1 + m_2 S_2 = S_0, \\ m_1 D_{11} + m_2 D_{12} = D_0, & m_1 D_{12} + m_2 D_{22} = 0, \\ S_i^2 \geq D_{i1}^2 + D_{i2}^2, & \text{if } \varrho \in [0, 1], \\ S_i^2 \leq D_{i1}^2 + D_{i2}^2, & \text{if } \varrho \in [-1, 0] \end{array} \right\}$$

where

$$S_i = \frac{1}{m_i} \int_{Y_i} s(y) dy, \quad D_{ij} = \frac{1}{m_i} \int_{Y_i} d_j(y) dy, \quad i, j = 1, 2, \quad (7)$$

denote average spherical and deviatoric stresses in non-degenerate phases. It follows that $\Sigma \subseteq \Sigma_{\text{rel}}$ where

$$\Sigma_{\text{rel}} = \left\{ \tau : \tau \in \Sigma_{\text{uni}} \text{ and such that } S_i, D_{ij} \in \Sigma_{\text{av}}, \quad i, j = 1, 2 \right\} \quad (8)$$

stands for the set of relaxed stress fields, i.e. fields with neglected differential constraint $\text{div} \tau = 0$ in Y .

2.2. Composite materials of minimal stress energy

Energy bound and extremal effective material properties. The (quadrupled) stress energy density in Y_i , $i = 1, 2$, is calculated according to

$$U_i(\tau) = 4 [\tau : (A_i \tau)] = K_i s^2 + L_i (d_1^2 + d_2^2) \quad (9)$$

and we set $U_3(\tau) = 0$ due to assumed $\tau = 0$ in void. The contraction $\tau : (A_i \tau)$ is realized by a standard operation $[\tau]^T (A_i) [\tau]$ in the basis (2). Here $[\tau]$ and (A_i) stand for a vector and matrix representations of respective quantities and $[\tau]^T$ denotes a transpose of $[\tau]$. Effective energy is thus calculated according to

$$U_0(\varrho) = \inf \left\{ \sum_{i=1}^3 \int_{Y_i} U_i(\tau) dy \mid \tau \in \Sigma \right\} \quad (10)$$

and $U_0(\varrho)$ is bounded from below by

$$U_*(\varrho) = \inf \left\{ U_0(\varrho) \mid Y_i \text{ as in (1)} \right\}.$$

Bounding the stress energy allows for restricting the values of effective constitutive properties. Indeed, by introducing K_* , L_* and A_* linked similarly to (3) one may claim $U_*(\varrho)$ in the form

$$U_*(\varrho) = 4 [\tau_0 : (A_* \tau_0)] = K_* S_0^2 + L_* D_0^2 = \frac{1}{2} \left(K_* (1 + \varrho)^2 + L_* (1 - \varrho)^2 \right). \quad (11)$$

With this notation, K_* and L_* represent coupled bounds on effective moduli of a composite for fixed ϱ . They may be understood as constitutive properties of a homogenized medium adjusted to the external stress $\tau_0 = S_0 E_1 + D_0 E_2$ in a sense of storing the minimal amount of energy in two directions E_1 , E_2 simultaneously.

Note that in light of the above, the requirement of isotropy imposed on the effective medium is redundant. Indeed, the component of A_* related to the direction $E_3 \otimes E_3$ may be arbitrary as $\tau_0 : E_3 = 0$. Non-isotropic microstructures may thus be optimal, i.e. such that the amount of stress energy stored in them equals $U_*(\varrho)$. Details on this topic are presented in Sec. 4.

Let us find formulae for K_* and L_* . To this end, note that by varying $\varrho \in [-1, 1]$ on the r.h.s. of (11) we obtain a family of functions that are quadratic in ϱ and $U_*(\varrho)$ represents an envelope of this family. Solving the system

$$\begin{aligned} U_*(\varrho) - \frac{1}{2} \left(K_* (1 + \varrho)^2 + L_* (1 - \varrho)^2 \right) &= 0, \\ \frac{d}{d\varrho} \left[U_*(\varrho) - \frac{1}{2} \left(K_* (1 + \varrho)^2 + L_* (1 - \varrho)^2 \right) \right] &= 0, \end{aligned}$$

allows for determining the coefficients of $U_*(\varrho)$. They read

$$\begin{aligned} K_*(\varrho) &= \frac{U_*(\varrho)}{1 + \varrho} + \frac{1 - \varrho}{2(1 + \varrho)} \frac{dU_*(\varrho)}{d\varrho}, \\ L_*(\varrho) &= \frac{U_*(\varrho)}{1 - \varrho} - \frac{1 + \varrho}{2(1 - \varrho)} \frac{dU_*(\varrho)}{d\varrho}. \end{aligned} \quad (12)$$

Functions in (12) are extremal if their values belong to $\partial G_m A$, i.e. the boundary of G -closure of set A . Recall that $G_m A$ contains all effective

Hooke's tensors obtained by homogenization of components belonging to A , taken with arbitrary microstructure and fixed volume fractions m_i , see e.g. (Cherkaev, 2000) for further reference.

Calculating energy bound by the translation method. In what follows we briefly describe a procedure of determining $U_*(\varrho)$. For this we make use of *the translation method* which proved to be an efficient tool in solving problems regarding energy and effective property bounds posed in various settings, see (Cherkaev, 2000; Milton, 2002). The method starts from introducing *a translation parameter* $\alpha \in \mathbb{T} \subset \mathbb{R}$ and rephrasing (9) in the form

$$U_i(\tau) = F_i(\tau, \alpha) - 2\alpha \det \tau, \quad i = 1, 2,$$

where

$$F_i(\tau, \alpha) = (K_i + \alpha) s^2 + (L_i - \alpha) (d_1^2 + d_2^2).$$

With (4) taken into consideration we calculate

$$\sum_{i=1}^3 \int_{Y_i} U_i(\tau) dy = \sum_{i=1}^3 \int_{Y_i} F_i(\tau, \alpha) dy - 2\varrho \alpha.$$

Next, we neglect the differential constraints on the stress field in Y which allows for taking the infimum in (10) on the set enlarged from Σ to Σ_{rel} . Another effect of dropping $\text{div } \tau = 0$ in Y is that the optimal stress field $\tau \in \Sigma_{\text{rel}}$ can be determined independently in each phase. Moreover, the search can be reduced to non-degenerate phases only as $\tau = 0$ in void. Consequently, one obtains

$$\begin{aligned} U_0(\varrho) &\geq \Phi(\varrho, \alpha) - 2\varrho \alpha, \\ \Phi(\varrho, \alpha) &= \inf \left\{ \sum_{i=1}^2 \int_{Y_i} F_i(\tau, \alpha) dy \mid \tau \in \Sigma_{\text{rel}} \right\}. \end{aligned} \quad (13)$$

By (8) it is possible to split the latter task into two steps. First, we set

$$\Phi_i(S_i, D_{i1}, D_{i2}, \alpha) = \inf \left\{ \int_{Y_i} F_i(\tau, \alpha) dy \mid \tau \in \Sigma_{\text{uni}} \right\}, \quad i = 1, 2, \quad (14)$$

and we continue with

$$\Phi(\varrho, \alpha) = \min \left\{ \Phi_1 + \Phi_2 \mid S_i, D_{ij} \in \Sigma_{\text{av}} \right\}. \quad (15)$$

Stress energy estimation predicted by the translation method is thus given by

$$U_*(\varrho) \geq U_{\text{tr}}(\varrho) = \max \left\{ \Phi(\varrho, \alpha) - 2 \varrho \alpha \mid \alpha \in \mathbb{T} \right\} \quad (16)$$

and the equality $U_*(\varrho) = U_{\text{tr}}(\varrho)$ holds if $\tau \in \Sigma_{\text{rel}}$ solving (13), or equivalently (14) and (15), proves to be statically admissible, i.e. $\tau \in \Sigma$. This requirement is fulfilled if the stress field components in neighboring materials are consistent with $\text{div } \tau = 0$ in Y . If this is the case then formula for $U_{\text{tr}}(\varrho)$ is *optimal*, as it corresponds to the boundary of $G_m A$ and it may be substituted in (12) for calculating extremal coupled effective properties of a three-phase composite. Explicit calculations of $U_{\text{tr}}(\varrho)$ is a subject of Sec. 3, and proving its optimality is postponed for Sec. 4.

3. Lower bound on the stress energy: Sufficient condition of optimality

We proceed by explicit calculation of $\tau \in \Sigma_{\text{rel}}$ in two steps defined by (14) and (15). This in turn allows for determining $U_{\text{tr}}(\varrho)$ by proper adjustment of the translation parameter α in (16). Consequently, bounds on effective constitutive properties $K_*(\varrho)$ and $L_*(\varrho)$ related to $\partial G_m A$ are obtained through (12) under the assumption that energy bound predicted by the translation method is optimal, i.e. that $U_*(\varrho) = U_{\text{tr}}(\varrho)$ holds. Discussion of the latter is provided in Sections 4 and 5. Below we establish *the sufficient condition of optimality* in terms of stress fields related to $U_{\text{tr}}(\varrho)$. With K_i , L_i , $i = 1, 2$ given, the sought condition turns out to be dependent on mutual relations among m_1 , m_2 and ϱ . It results in the division of a polyhedron $\Pi = \{(\varrho, m_1, m_2) : \varrho \in [-1, 1], m_1 \in [0, 1 - m_2], m_2 \in [0, 1]\}$ into several regions of optimality. Table 1 provides a brief guide to the sequence and results of calculations and Fig. 2 shows an exemplary cross-section of Π by a plane $m_2 = \text{const.}$

Table 1: A guide to calculations of the lower bound on the stress energy, related effective constitutive properties and sufficient condition of optimality.

range of ϱ	regions in Fig. 2	bound $U_{\text{tr}}(\varrho)$	$K_*(\varrho)$ and $L_*(\varrho)$	sufficient condition
$\varrho \in [-1, 0]$	A'	(42)	(51)	(21), (24) and (44)
	B'	(36)	(53)	(17), (21) and (37)
	C'	(39)	(54)	(17), (21) and (40)
	D'	(48)	(56) ^a	(17), (24) and (49)
$\varrho \in [0, 1]$	D	(46)	(55) ^a	(17), (20) and (47)
	C	(30)	(54)	(17), (19) and (31)
	B	(27)	(52)	(17), (19) and (28)
	A	(33)	(50)	(19), (20) and (34)
unrestricted	E	—	—	—

^a For remarks on regions D, D', see Sec. 5.

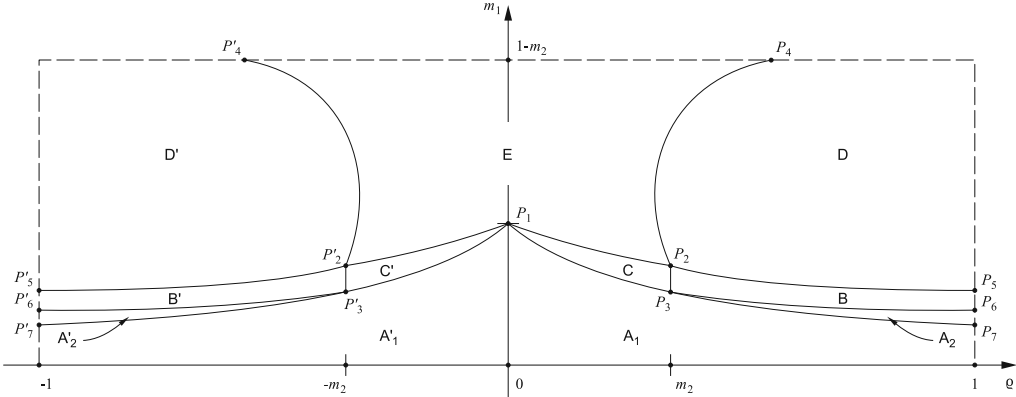


Figure 2: Regions of optimality related to a cross-section of a polyhedron Π by a plane $m_2 = 0.35$. Constitutive properties of nondegenerate materials are fixed to $K_1 = 1$, $L_1 = 2$, $K_2 = 3$, $L_2 = 4$.

3.1. Stress fields in phases

In (14) we wish to obtain $\Phi_i(S_i, D_{i1}, D_{i2}, \alpha) > -\infty$ for $i = 1, 2$, as such property is crucial in subsequent derivation of a nontrivial energy bound $U_{\text{tr}}(\varrho)$. To this end, we first discuss the conditions under which the integrand

$F_i(\tau, \alpha)$ is bounded from below by a convex function. Next, we determine optimal relaxed stress fields $\tau \in \Sigma_{\text{uni}}$ by making use of the Jensen inequality, see (Cherkaev, 2000, Sec. 1.2). Applied to our case, it states that if $F_i(\tau, \alpha)$ is convex in τ then its integral over Y_i takes a minimum value on a constant stress field being the average of τ over Y_i . Thus, with τ decomposed into spherical and deviatoric parts, we expect the minimizers to be expressed in terms of averages S_i, D_{i1}, D_{i2} .

Assuming that $S_i, D_{ij}, i, j = 1, 2$, are prescribed and $K_i \neq L_i$, we consider the following cases:

- (I) If $\alpha \in (-K_i, L_i)$ then all terms in $F_i(\tau, \alpha)$ are convex.

For $\varrho \in [-1, 1]$, from the Jensen inequality it follows that

$$\Phi_i(S_i, D_{i1}, D_{i2}, \alpha) = m_i(K_i + \alpha) S_i^2 + m_i(L_i - \alpha) (D_{i1}^2 + D_{i2}^2).$$

Components of optimal relaxed field $\tau \in \Sigma_{\text{uni}}$ are constant in Y_i and read

$$s(y) = S_i, \quad d_j(y) = D_{ij} \quad \text{a.e. in } Y_i. \quad (17)$$

- (IIa) If $\alpha > L_i$ then the s -term in $F_i(\tau, \alpha)$ is convex and d -terms are concave. For $\varrho \in [0, 1]$ we have $s^2 \geq d_1^2 + d_2^2$ a.e. in Y_i hence $F_i(\tau, \alpha)$ is bounded from below by a convex function. Indeed,

$$(K_i + \alpha) s^2 + (L_i - \alpha) (d_1^2 + d_2^2) \geq (K_i + L_i) s^2$$

and the “ $\geq$ ” relation above is replaced by “ $=$ ” when $s^2 = d_1^2 + d_2^2$ a.e. in Y_i . Consequently,

$$\Phi_i(S_i, D_{i1}, D_{i2}, \alpha) = m_i(K_i + L_i) S_i^2. \quad (18)$$

Components of optimal $\tau \in \Sigma_{\text{uni}}$ are given by

$$\begin{aligned} s(y) &= S_i \text{ (constant field),} \\ d_1(y) &= S_i \cos \theta(y), \quad d_2(y) = S_i \sin \theta(y), \quad \text{a.e. in } Y_i \end{aligned} \quad (19)$$

with $\theta(y)$ arbitrary in Y_i up to the restrictions given in (7).

- (IIb) If $\alpha = L_i$ then the s -term in $F_i(\tau, \alpha)$ is convex and d -terms vanish. For $\varrho \in [0, 1]$ we obtain $\Phi_i(S_i, D_{i1}, D_{i2}, \alpha)$ in a form identical to (18). Formulae determining the components of optimal relaxed field read

$$\begin{aligned} s(y) &= S_i \text{ (constant field),} \\ d_j(y) &\text{ arbitrary up to } s^2 \geq d_1^2 + d_2^2 \text{ a.e. in } Y_i. \end{aligned} \quad (20)$$

(IIIa) If $\alpha < -K_i$ then the s -term in $F_i(\tau, \alpha)$ is concave and d -terms are convex.

For $\varrho \in [-1, 0]$ we have $s^2 \leq d_1^2 + d_2^2$ a.e. in Y_i hence

$$(K_i + \alpha) s^2 + (L_i - \alpha) (d_1^2 + d_2^2) \geq (K_i + L_i) (d_1^2 + d_2^2) \quad (21)$$

and the “ $\geq$ ” relation above is replaced by “ $=$ ” when $s^2 = d_1^2 + d_2^2$ a.e. in Y_i . Consequently,

$$\Phi_i(S_i, D_{i1}, D_{i2}, \alpha) = m_i(K_i + L_i) (D_{i1}^2 + D_{i2}^2). \quad (22)$$

Components of optimal relaxed stress field are constant in Y_i and given by

$$s(y) = \pm \sqrt{D_{i1}^2 + D_{i2}^2}, \quad d_j(y) = D_{ij} \text{ a.e. in } Y_i. \quad (23)$$

(IIIb) If $\alpha = -K_i$ then the s -term in $F_i(\tau, \alpha)$ vanishes and d -terms are convex. For $\varrho \in [-1, 0]$ we obtain $\Phi_i(S_i, D_{i1}, D_{i2}, \alpha)$ in the form identical to (22) with optimal relaxed fields

$$\begin{aligned} s(y) &\text{ arbitrary up to } s^2 \leq d_1^2 + d_2^2, \text{ a.e. in } Y_i, \\ d_j(y) &= D_{ij} \text{ (constant field)}. \end{aligned} \quad (24)$$

Other relations between ϱ and α are not discussed here as they are irrelevant in further study.

3.2. Calculation of the energy bound: Regions of optimality

Having $\Phi_i = \Phi_i(S_i, D_{i1}, D_{i2}, \alpha)$, $i = 1, 2$, explicitly calculated, we now turn to the problem of determining $\Phi(\varrho, \alpha)$ and $U_{\text{tr}}(\varrho)$ through (15) and (16). Moreover, substituting optimal S_i, D_{ij} in the formulae for $s(y)$ and $d_j(y)$ leads to sufficient optimality condition of the translation energy bound in terms of a stress field in i -th phase.

3.2.1. Case of $\varrho \in [0, 1]$ and $\alpha \in (L_1, L_2)$: Regions **B** and **C**

According to the discussion in Sec. 3.1, items (I) and (IIa), set

$$\begin{aligned} \Phi_1 &= m_1(K_1 + L_1) S_1^2, \\ \Phi_2 &= m_2(K_2 + \alpha) S_2^2 + m_2(L_2 - \alpha) (D_{21}^2 + D_{22}^2). \end{aligned}$$

It follows that

$$\begin{aligned}
\Phi(\varrho, \alpha) = & \min \{ \Phi_1 + \Phi_2 \} \\
& \text{subject to: } m_1 S_1 + m_2 S_2 = S_0, \\
& m_1 D_{11} + m_2 D_{21} = D_0, \\
& m_1 D_{12} + m_2 D_{22} = 0, \\
& S_1^2 \geq D_{11}^2 + D_{12}^2, \\
& S_2^2 \geq D_{21}^2 + D_{22}^2.
\end{aligned} \tag{25}$$

From the KKT optimality conditions we conclude that: (i) $D_{12} = D_{22} = 0$, (ii) $\Phi_1 + \Phi_2$ is minimized with respect to D_{21} if D_{11} is maximized. All constraints in (25) are satisfied if we set

$$D_{11} = \min \left\{ \frac{1}{m_1} D_0, S_1 \right\}.$$

Consequently, further discussion splits into two subcases corresponding to regions of optimality B and C in Fig. 2. Forthcoming results are rather straightforward to obtain in both regions, hence we omit the details of calculations.

Region B : Assume that

$$D_{11} = \frac{1}{m_1} D_0 \leq S_1.$$

By this, $D_{21} = 0$ and (25) transforms to

$$\begin{aligned}
\Phi(\varrho, \alpha) = & \min \left\{ m_1(K_1 + L_1) S_1^2 + m_2(K_2 + \alpha) S_2^2 \right\} \\
& \text{subject to: } m_1 S_1 + m_2 S_2 = S_0,
\end{aligned} \tag{26}$$

hence one may replace the above with a one-dimensional unconstrained optimization problem where S_1 is treated as a variable. The necessary condition of optimality $\partial(\Phi_1 + \Phi_2)/\partial S_1 = 0$ allows for determining the function $S_1(\alpha)$ which is substituted back in (26), and formula for $S_2(\alpha)$ follows from the constraint. The lower bound on stress energy in region B given by

$$\begin{aligned}
U_{\text{tr}}(\varrho) &= \max \left\{ \Phi(\varrho, \alpha) - 2\varrho\alpha \mid \alpha \in (L_1, L_2) \right\} = \\
&= \frac{(1 + \varrho - 2\sqrt{\varrho m_2})^2}{2m_1} (K_1 + L_1) + 2\varrho K_2
\end{aligned} \tag{27}$$

results from solving $\partial[\Phi(\varrho, \alpha) - 2\varrho\alpha]/\partial\alpha = 0$. In this way, two critical values of α are obtained. The one corresponding to maximum in (27) reads

$$\alpha = \frac{1}{2} \frac{\sqrt{\varrho m_2}(1 + \varrho - 2\sqrt{\varrho m_2})}{\varrho m_1} (K_1 + L_1) - K_2.$$

Consequently, optimal mean spherical and deviatoric stress components in region B are given by

$$\begin{aligned} S_1 &= \frac{1 + \varrho - 2\sqrt{\varrho m_2}}{\sqrt{2} m_1}, & D_{11} &= \frac{1 - \varrho}{\sqrt{2} m_1}, & D_{12} &= 0, \\ S_2 &= \sqrt{2} \frac{\sqrt{\varrho m_2}}{m_2}, & D_{21} &= 0, & D_{22} &= 0. \end{aligned} \quad (28)$$

Sufficient optimality condition of (27) expressed in terms of stress fields in phases 1 and 2 respectively follow from substituting S_1, D_{11}, D_{12} in (19) and S_2, D_{21}, D_{22} in (17).

Region B is represented by a curvilinear rectangle $P_2P_3P_5P_6$ in Fig. 2. Its boundaries are determined according to the following scheme

$$\begin{aligned} \alpha < L_2 &\Rightarrow m_1 > \psi_{A-B}(m_2, \varrho), \\ \alpha > L_1 &\Rightarrow m_1 < \psi_{B-D}(m_2, \varrho), \\ m_1 S_1 \geq D_0 &\Rightarrow \varrho \in [m_2, 1] \end{aligned}$$

where

$$\begin{aligned} \psi_{A-B}(m_2, \varrho) &= \frac{\sqrt{\varrho m_2}(1 + \varrho - 2\sqrt{\varrho m_2})}{2\varrho} \frac{K_1 + L_1}{K_2 + L_2}, \\ \psi_{B-D}(m_2, \varrho) &= \frac{\sqrt{\varrho m_2}(1 + \varrho - 2\sqrt{\varrho m_2})}{2\varrho} \frac{K_1 + L_1}{K_2 + L_1}. \end{aligned} \quad (29)$$

Region C : Conversely to previous paragraph assume

$$D_{11} = S_1 \leq \frac{1}{m_1} D_0,$$

which results in

$$\begin{aligned} \Phi(\varrho, \alpha) &= \min \left\{ m_1(K_1 + L_1) S_1^2 + \right. \\ &\quad \left. + m_2[(K_2 + \alpha) S_2^2 + (L_2 - \alpha) D_{21}^2] \right\} \\ &\text{subject to: } m_1 S_1 + m_2 S_2 = S_0, \\ &\quad m_1 S_1 + m_2 D_{21} = D_0. \end{aligned}$$

The algorithm of calculations is similar to the one presented for region B. It follows that the stress energy in region C is bounded from below by

$$\begin{aligned}
U_{\text{tr}}(\varrho) &= \max \left\{ \Phi(\varrho, \alpha) - 2\varrho\alpha \mid \alpha \in (L_1, L_2) \right\} = \\
&= \frac{(K_2 + L_2)\varrho^2}{2m_2} + (K_2 - L_2)\varrho + \\
&\quad + \frac{(K_1 + L_1)(1 - m_2)^2 + (K_2 + L_2)m_1m_2}{2m_1}
\end{aligned} \tag{30}$$

with

$$\alpha = \frac{1}{2} \left\{ (L_2 - K_2) + \frac{m_2}{\varrho m_1} [(1 - m_2)(K_1 + L_1) - m_1(K_2 + L_2)] \right\},$$

and

$$\begin{aligned}
S_1 &= \frac{1 - m_2}{\sqrt{2}m_1}, \quad D_{11} = S_1, \quad D_{12} = 0, \\
S_2 &= \frac{m_2 + \varrho}{\sqrt{2}m_2}, \quad D_{21} = \frac{m_2 - \varrho}{\sqrt{2}m_2}, \quad D_{22} = 0.
\end{aligned} \tag{31}$$

By substituting (31) in (19) and (17) respectively we obtain sufficient optimality condition of (30) in terms of stress fields in phases 1 and 2.

Region C is represented in Fig. 2 by a curvilinear triangle $P_1P_2P_3$. Its boundaries are determined by the following expressions

$$\begin{aligned}
\alpha < L_2 &\Rightarrow m_1 > \psi_{\text{A-C}}(m_2, \varrho), \\
\alpha > L_1 &\Rightarrow m_1 < \psi_{\text{C-E}}(m_2, \varrho), \\
m_1 S_1 \leq D_0 &\Rightarrow \varrho \in [0, m_2]
\end{aligned}$$

where

$$\begin{aligned}
\psi_{\text{A-C}}(m_2, \varrho) &= \frac{m_2(1 - m_2)(K_1 + L_1)}{(m_2 + \varrho)(K_2 + L_2)}, \\
\psi_{\text{C-E}}(m_2, \varrho) &= \frac{m_2(1 - m_2)(K_1 + L_1)}{(m_2 + \varrho)(K_2 + L_2) - 2(L_2 - L_1)\varrho}.
\end{aligned} \tag{32}$$

3.2.2. Case of $\varrho \in [0, 1]$ and $\alpha > L_2$: Region A

According to the discussion in Sec. 3.1, item (IIa), set

$$\Phi_i = m_i(K_i + L_i) S_i^2, \quad i = 1, 2.$$

Hence

$$\begin{aligned} \Phi(\varrho, \alpha) = & \min \{ \Phi_1 + \Phi_2 \} \\ & \text{subject to: } m_1 S_1 + m_2 S_2 = S_0 \end{aligned}$$

and

$$U_{\text{tr}}(\varrho) = \max \left\{ \Phi(\varrho, \alpha) - 2\varrho\alpha \mid \alpha \geq L_2 \right\}.$$

It is immediate that the function to be maximized monotonically decreases in α hence we set $\alpha = L_2$. Results obtained in the remainder of this section correspond to the region of optimality **A** in Fig. 2.

Region A : Proceeding analogously to previous cases we derive the lower estimate of stress energy in region **A**. It takes the form

$$U_{\text{tr}}(\varrho) = \frac{(1+\varrho)^2}{2} \frac{(K_1 + L_1)(K_2 + L_2)}{m_1(K_2 + L_2) + m_2(K_1 + L_1)} - 2\varrho L_2. \quad (33)$$

Optimal values of mean spherical components of stresses read

$$\begin{aligned} S_1 &= \frac{1+\varrho}{\sqrt{2}} \frac{K_2 + L_2}{m_1(K_2 + L_2) + m_2(K_1 + L_1)}, \\ S_2 &= \frac{1+\varrho}{\sqrt{2}} \frac{K_1 + L_1}{m_1(K_2 + L_2) + m_2(K_1 + L_1)}. \end{aligned} \quad (34)$$

Substituting S_1 and S_2 in (19) and (20) leads to sufficient optimality condition of (33) in terms of stress fields in phases 1 and 2 respectively.

For fixed $K_i, L_i, i = 1, 2$, and arbitrary m_2 , region **A** is described by

$$\begin{aligned} \mathbf{A} = \left\{ (\varrho, m_1): \right. & 0 \leq m_1 \leq \psi_{\mathbf{A}-\mathbf{C}}(m_2, \varrho) \text{ if } \varrho \in [0, m_2], \\ & 0 \leq m_1 \leq \psi_{\mathbf{A}-\mathbf{B}}(m_2, \varrho) \text{ if } \varrho \in [m_2, 1] \left. \right\} \end{aligned}$$

see (29) and (32). Curvilinear sides of **A** are represented in Fig. 2 by lines P_1P_3 and P_3P_6 . Note that **A** splits into **A**₁ and **A**₂ with the interface represented by a curve P_3P_7 . This division is explained in Sec. 4.2.3.

*3.2.3. Case of $\varrho \in [-1, 0]$ and $\alpha \in (-K_2, -K_1)$: Regions **B'** and **C'***

According to the discussion in Sec. 3.1, items (I) and (IIIa), set

$$\begin{aligned} \Phi_1 &= m_1(K_1 + L_1) (D_{11}^2 + D_{12}^2), \\ \Phi_2 &= m_2(K_2 + \alpha) S_2^2 + m_2(L_2 - \alpha) (D_{21}^2 + D_{22}^2). \end{aligned}$$

It follows that

$$\begin{aligned}
\Phi(\varrho, \alpha) = & \min \{ \Phi_1 + \Phi_2 \} \\
\text{subject to: } & m_1 S_1 + m_2 S_2 = S_0, \\
& m_1 D_{11} + m_2 D_{21} = D_0, \\
& m_1 D_{12} + m_2 D_{22} = 0, \\
& S_1^2 \leq D_{11}^2 + D_{12}^2, \\
& S_2^2 \leq D_{21}^2 + D_{22}^2.
\end{aligned} \tag{35}$$

From the KKT optimality conditions we conclude that: (i) $D_{12} = D_{22} = 0$, (ii) S_2 minimizes $\Phi_1 + \Phi_2$ if S_1 takes its maximal value. All constraints in (35) are satisfied if we set

$$S_1 = \min \left\{ \frac{1}{m_1} S_0, D_{11} \right\}.$$

Similarly to Sec. 3.2.1, the case splits into two subcases. They correspond to regions of optimality B' and C' in Fig. 2.

Region B' : Assume that

$$S_1 = \frac{1}{m_1} S_0 \leq D_{11}.$$

By this, $S_2 = 0$ and (35) transforms to

$$\begin{aligned}
\Phi(\varrho, \alpha) = & \min \left\{ m_1 (K_1 + L_1) D_{11}^2 + m_2 (K_2 + \alpha) D_{21}^2 \right\} \\
\text{subject to: } & m_1 D_{11} + m_2 D_{21} = D_0.
\end{aligned}$$

Proceeding analogously to previous sections we obtain

$$\begin{aligned}
U_{\text{tr}}(\varrho) &= \max \left\{ \Phi(\varrho, \alpha) - 2\varrho\alpha \mid \alpha \in (-K_2, -K_1) \right\} = \\
&= \frac{(1 - \varrho - 2\sqrt{-\varrho m_2})^2}{2m_1} (K_1 + L_1) - 2\varrho L_2
\end{aligned} \tag{36}$$

with

$$\alpha = \frac{1}{2} \frac{\sqrt{-\varrho m_2} (1 - \varrho - 2\sqrt{-\varrho m_2})}{\varrho m_1} (K_1 + L_1) + L_2.$$

Optimal mean values of spherical and deviatoric components of stresses in region $\mathbf{B}'$ are thus given by

$$\begin{aligned} S_1 &= \frac{1 + \varrho}{\sqrt{2} m_1}, \quad D_{11} = \frac{1 - \varrho - 2\sqrt{-\varrho m_2}}{\sqrt{2} m_1}, \quad D_{12} = 0, \\ S_2 &= 0, \quad D_{21} = \sqrt{2} \frac{\sqrt{-\varrho m_2}}{m_2}, \quad D_{22} = 0. \end{aligned} \quad (37)$$

Sufficient condition of optimality of (36) result from substituting S_1 , D_{11} , D_{12} in (23) and (17).

Region $\mathbf{B}'$ is represented by a curvilinear rectangle $P'_2 P'_3 P'_5 P'_6$ in Fig. 2. Its boundaries are determined according to the following scheme

$$\begin{aligned} \alpha > -K_2 &\Rightarrow m_1 > \psi_{\mathbf{A}'-\mathbf{B}'}(m_2, \varrho), \\ \alpha < -K_1 &\Rightarrow m_1 < \psi_{\mathbf{B}'-\mathbf{D}'}(m_2, \varrho), \\ m_1 D_{11} \geq S_0 &\Rightarrow \varrho \in [-1, -m_2] \end{aligned}$$

where

$$\begin{aligned} \psi_{\mathbf{A}'-\mathbf{B}'}(m_2, \varrho) &= -\frac{\sqrt{-\varrho m_2}(1 - \varrho - 2\sqrt{-\varrho m_2})}{2\varrho} \frac{K_1 + L_1}{K_2 + L_2}, \\ \psi_{\mathbf{B}'-\mathbf{D}'}(m_2, \varrho) &= -\frac{\sqrt{-\varrho m_2}(1 - \varrho - 2\sqrt{-\varrho m_2})}{2\varrho} \frac{K_1 + L_1}{K_1 + L_2}. \end{aligned} \quad (38)$$

Region $\mathbf{C}'$: Conversely to previous paragraph assume

$$S_1 = D_{11} \leq \frac{1}{m_1} S_0,$$

which results in

$$\begin{aligned} \Phi(\varrho, \alpha) &= \min \left\{ m_1(K_1 + L_1) D_{11}^2 + \right. \\ &\quad \left. + m_2[(K_2 + \alpha) S_2^2 + (L_2 - \alpha) D_{21}^2] \right\} \\ &\text{subject to: } m_1 D_{11} + m_2 S_2 = S_0, \\ &\quad m_1 D_{11} + m_2 D_{21} = D_0. \end{aligned}$$

It follows that the stress energy in region $\mathbf{C}'$ is bounded from below by

$$\begin{aligned} U_{\text{tr}}(\varrho) &= \max \left\{ \Phi(\varrho, \alpha) - 2\varrho\alpha \mid \alpha \in (-K_2, -K_1) \right\} = \\ &= \frac{(K_2 + L_2)\varrho^2}{2m_2} + (K_2 - L_2)\varrho + \\ &\quad + \frac{(K_1 + L_1)(1 - m_2)^2 + (K_2 + L_2)m_1 m_2}{2m_1} \end{aligned} \quad (39)$$

with

$$\alpha = \frac{1}{2} \left\{ (L_2 - K_2) - \frac{m_2}{\varrho m_1} [(1 - m_2)(K_1 + L_1) - m_1(K_2 + L_2)] \right\},$$

and

$$\begin{aligned} S_1 &= \frac{1 - m_2}{\sqrt{2} m_1}, & D_{11} &= S_1, & D_{12} &= 0, \\ S_2 &= \frac{m_2 + \varrho}{\sqrt{2} m_2}, & D_{21} &= \frac{m_2 - \varrho}{\sqrt{2} m_2}, & D_{22} &= 0. \end{aligned} \quad (40)$$

Substituting S_1 , D_{11} , D_{12} in (23) and S_2 , D_{21} , D_{22} in (17) results in sufficient optimality condition of (39).

Region C' is represented in Fig. 2 by a curvilinear triangle $P_1 P_2' P_3'$. Its boundaries are determined by the following expressions

$$\begin{aligned} \alpha > -K_2 &\Rightarrow m_1 > \psi_{A'-C'}(m_2, \varrho), \\ \alpha < -K_1 &\Rightarrow m_1 < \psi_{C'-E}(m_2, \varrho), \\ m_1 D_{11} \leq S_0 &\Rightarrow \varrho \in [-m_2, 0] \end{aligned}$$

where

$$\begin{aligned} \psi_{A'-C'}(m_2, \varrho) &= \frac{m_2(1 - m_2)(K_1 + L_1)}{(m_2 - \varrho)(K_2 + L_2)}, \\ \psi_{C'-E}(m_2, \varrho) &= \frac{m_2(1 - m_2)(K_1 + L_1)}{(m_2 + \varrho)(K_2 + L_2) - 2(L_2 + K_1)\varrho}. \end{aligned} \quad (41)$$

3.2.4. Case of $\varrho \in [-1, 0]$ and $\alpha < -K_2$: Region A'

According to the discussion in Sec. 3.1, item (IIIa), set

$$\Phi_i = m_i(K_i + L_i) (D_{i1}^2 + D_{i2}^2), \quad i = 1, 2.$$

Hence

$$\begin{aligned} \Phi(\varrho, \alpha) &= \min \{ \Phi_1 + \Phi_2 \} \\ &\text{subject to: } m_1 D_{11} + m_2 D_{21} = D_0, \\ &\quad m_1 D_{12} + m_2 D_{22} = 0, \end{aligned}$$

and it is immediate that $D_{12} = D_{22} = 0$.

The estimate of the stress energy is determined as

$$U_{\text{tr}}(\varrho) = \max \left\{ \Phi(\varrho, \alpha) - 2\varrho\alpha \mid \alpha \leq -K_2 \right\}. \quad (42)$$

Function to be maximized in (42) monotonically decreases in α hence we set $\alpha = -K_2$. Results obtained in the remainder of this section correspond to the region of optimality A' in Fig. 2.

Region A' : The lower estimate of stress energy in region A' takes the form

$$U_{\text{tr}}(\varrho) = \frac{(1 - \varrho)^2}{2} \frac{(K_1 + L_1)(K_2 + L_2)}{m_1(K_2 + L_2) + m_2(K_1 + L_1)} + 2\varrho K_2. \quad (43)$$

Optimal values of mean spherical fields read

$$\begin{aligned} D_{11} &= \frac{1 - \varrho}{\sqrt{2}} \frac{K_2 + L_2}{m_1(K_2 + L_2) + m_2(K_1 + L_1)}, \\ D_{21} &= \frac{1 - \varrho}{\sqrt{2}} \frac{K_1 + L_1}{m_1(K_2 + L_2) + m_2(K_1 + L_1)}. \end{aligned} \quad (44)$$

Considering (44) in (23) and (24) leads to sufficient optimality condition of (43) in terms of stress fields in phases 1 and 2 respectively.

For fixed K_i , L_i , $i = 1, 2$, region A' is described by

$$\begin{aligned} \mathbf{A}' = \left\{ (\varrho, m_1, m_2) : \right. & 0 \leq m_1 \leq \psi_{\mathbf{A}'-\mathbf{C}'}(m_2, \varrho) \text{ if } \varrho \in [-m_2, 0], \\ & \left. 0 \leq m_1 \leq \psi_{\mathbf{A}'-\mathbf{B}'}(m_2, \varrho) \text{ if } \varrho \in [-1, m_2] \right\} \end{aligned}$$

see (38) and (41). Curvilinear sides of A' are represented in Fig. 2 by lines $P_1P'_3$ and $P'_3P'_6$. Note that A' splits into $\mathbf{A}'_1$ and $\mathbf{A}'_2$ with the interface represented by a curve $P'_3P'_7$. This division is explained in Sec. 4.2.3.

3.2.5. Case of $\varrho \in [-1, 1]$ and $\alpha \in (-K_1, L_1)$: Regions D, D' and E

The case of $\alpha \in (-K_1, L_1)$ is discussed in Sec. 3.1, item (I). Both Φ_1 and Φ_2 are described by

$$\Phi_i = m_i \left[(K_i + \alpha) S_i^2 + (L_i - \alpha) (D_{i1}^2 + D_{i2}^2) \right], \quad i = 1, 2.$$

For $\varrho \in [0, 1]$ it follows that

$$\begin{aligned} \Phi(\varrho, \alpha) &= \min \{ \Phi_1 + \Phi_2 \} \\ \text{subject to: } & m_1 S_1 + m_2 S_2 = S_0, \\ & m_1 D_{11} + m_2 D_{21} = D_0, \\ & m_1 D_{12} + m_2 D_{22} = 0, \\ & S_1^2 \geq D_{11}^2 + D_{12}^2, \\ & S_2^2 \geq D_{21}^2 + D_{22}^2. \end{aligned} \quad (45)$$

In case of $\varrho \in [-1, 0]$, last two constraints change into

$$\begin{aligned} S_1^2 &\leq D_{11}^2 + D_{12}^2, \\ S_2^2 &\leq D_{21}^2 + D_{22}^2. \end{aligned}$$

The KKT requirements are that $D_{12} = D_{22} = 0$. Hence, in case of arbitrary ϱ , problem (45) takes the form

$$\begin{aligned} \Phi(\varrho, \alpha) = \min & \left\{ m_1 [(K_1 + \alpha) S_1^2 + (L_1 - \alpha) D_{11}^2] + \right. \\ & \left. + m_2 [(K_2 + \alpha) S_2^2 + (L_2 - \alpha) D_{21}^2] \right\} \\ \text{subject to: } & m_1 S_1 + m_2 S_2 = S_0, \\ & m_1 D_{11} + m_2 D_{21} = D_0. \end{aligned}$$

Applying necessary conditions of optimality leads to

$$\begin{aligned} S_1 &= \frac{(K_2 + \alpha) S_0}{m_1(K_2 + \alpha) + m_2(K_1 + \alpha)}, \quad D_{11} = \frac{(L_2 - \alpha) D_0}{m_1(L_2 - \alpha) + m_2(L_1 - \alpha)}, \\ S_2 &= \frac{(K_1 + \alpha) S_0}{m_1(K_2 + \alpha) + m_2(K_1 + \alpha)}, \quad D_{21} = \frac{(L_1 - \alpha) D_0}{m_1(L_2 - \alpha) + m_2(L_1 - \alpha)}. \end{aligned}$$

Technically, determining $U_{\text{tr}}(\varrho)$ and optimal $\alpha \in (-K_1, L_1)$ requires similar algorithm to the one used in previous sections. Corresponding formulae are not presented here due to their complexity. The limiting cases of $\alpha = L_1$ or $\alpha = -K_1$ are dealt with separately in the sequel of this Section. As a result, three additional regions of optimality appear. Namely, region **E** corresponds to $\alpha \in (-K_1, L_1)$ and regions **D** and **D'** are related to $\alpha = L_1$ and $\alpha = -K_1$ respectively.

Region E : The problem is now to find the formulae for two curves which separate region **E** from **D** and **D'**. These curves are given by implicit functions $\psi_{\text{D-E}}(m_1, m_2, \varrho) = 0$ and $\psi_{\text{D'-E}}(m_1, m_2, \varrho) = 0$ where

$$\begin{aligned} \psi_{\text{D-E}}(m_1, m_2, \varrho) &= \frac{\partial}{\partial \alpha} [\Phi(\varrho, \alpha) - 2 \varrho \alpha] \Big|_{\alpha=L_1}, \\ \psi_{\text{D'-E}}(m_1, m_2, \varrho) &= \frac{\partial}{\partial \alpha} [\Phi(\varrho, \alpha) - 2 \varrho \alpha] \Big|_{\alpha=-K_1}. \end{aligned}$$

It follows that

$$\begin{aligned}\psi_{\text{D-E}}(m_1, m_2, \varrho) &= \widehat{\psi}_{\text{D-E}}(m_1, m_2)(1 + \varrho)^2 + \frac{2\varrho(1 - m_1)}{m_1}, \\ \widehat{\psi}_{\text{D-E}}(m_1, m_2) &= \\ &= -\frac{m_2(K_1 + L_1)[(m_1 + m_2)(K_1 + L_1) + 2m_1(K_2 - K_1)]}{2m_1[m_1(K_2 + L_1) + m_2(K_1 + L_1)]^2},\end{aligned}$$

and

$$\begin{aligned}\psi_{\text{D'-E}}(m_1, m_2, \varrho) &= \widehat{\psi}_{\text{D'-E}}(m_1, m_2)(1 - \varrho)^2 + \frac{2\varrho(1 - m_1)}{m_1}, \\ \widehat{\psi}_{\text{D'-E}}(m_1, m_2) &= \\ &= \frac{m_2(K_1 + L_1)[(m_1 + m_2)(K_1 + L_1) + 2m_1(L_2 - L_1)]}{2m_1[m_1(K_1 + L_2) + m_2(K_1 + L_1)]^2}.\end{aligned}$$

Region E is bounded by the lines

$$\begin{aligned}m_1 &= 1 - m_2, \\ m_1 &= \psi_{\text{C'-E}} && \text{if } \varrho \in [-1, 0], \\ m_1 &= \psi_{\text{C-E}} && \text{if } \varrho \in [0, 1], \\ \psi_{\text{D'-E}}(m_1, m_2, \varrho) &= 0, \\ \psi_{\text{D-E}}(m_1, m_2, \varrho) &= 0,\end{aligned}$$

see (32) and (41). Curvilinear sides of E described above are respectively represented in Fig. 2 by lines $P_1P'_3$, P_1P_3 , $P'_2P'_4$ and P_2P_4 .

Region D : Assuming $\alpha = L_1$ and repeating the discussion for region E or region B (Sec. 3.2.1) we conclude that the stress energy estimation and optimal mean fields in D are given by

$$U_{\text{tr}}(\varrho) = \frac{(1 + \varrho)^2}{2} \frac{(K_1 + L_1)(K_2 + L_1)}{m_1(K_2 + L_1) + m_2(K_1 + L_1)} - 2\varrho L_1. \quad (46)$$

and

$$\begin{aligned}S_1 &= \frac{(K_2 + L_1)(1 + \varrho)}{\sqrt{2}[m_1(K_2 + L_1) + m_2(K_1 + L_1)]}, & D_{11} &= \frac{1 - \varrho}{\sqrt{2}m_1}, & D_{12} &= 0, \\ S_2 &= \frac{(K_1 + L_1)(1 + \varrho)}{\sqrt{2}[m_1(K_2 + L_1) + m_2(K_1 + L_1)]}, & D_{21} &= 0, & D_{22} &= 0.\end{aligned} \quad (47)$$

Region D is represented in Fig. 2 by an area bounded by two straight lines: (i) $\varrho = 1$, (ii) $m_1 = 1 - m_2$ and two curves: (i) $\psi_{D-E}(m_1, m_2, \varrho) = 0$ (line P_2P_4), (ii) $m_1 = \psi_{B-D}$ (line P_2P_5).

Region D' : Assuming $\alpha = -K_1$ and repeating the discussion for region E or region B' (Sec. 3.2.3) we conclude that the stress energy estimation and optimal mean fields in D' are given by

$$U_{tr}(\varrho) = \frac{(1 - \varrho)^2}{2} \frac{(K_1 + L_1)(K_1 + L_2)}{m_1(K_1 + L_2) + m_2(K_1 + L_1)} + 2\varrho K_1. \quad (48)$$

and

$$\begin{aligned} S_1 &= \frac{1 + \varrho}{\sqrt{2} m_1}, & D_{11} &= \frac{(K_1 + L_2)(1 - \varrho)}{\sqrt{2} [m_1(K_1 + L_2) + m_2(K_1 + L_1)]}, & D_{12} &= 0, \\ S_2 &= 0, & D_{21} &= \frac{(K_1 + L_1)(1 - \varrho)}{\sqrt{2} [m_1(K_1 + L_2) + m_2(K_1 + L_1)]}, & D_{22} &= 0. \end{aligned} \quad (49)$$

Region D' is represented in Fig. 2 by an area bounded by two straight lines: (i) $\varrho = -1$, (ii) $m_1 = 1 - m_2$ and two curves: (i) $\psi_{D'-E}(m_1, m_2, \varrho) = 0$ (line $P'_2P'_4$), (ii) $m_1 = \psi_{B'-D'}$ (line $P'_2P'_5$).

Sufficient condition of optimality of (46) result from substituting (49) in (20) and (17). Similarly, considering (49) in (24) and (17) leads to sufficient optimality condition of (48).

3.3. Bounds on effective isotropic properties

Making use of (12) allows for calculating bounds on effective isotropic properties in each optimality region where $U_*(\varrho)$ is determined. From the results obtained in the preceeding section and by assuming that $U_{tr}(\varrho) = U_*(\varrho)$ it follows that formulae for $K_*(\varrho)$ and $L_*(\varrho)$ can be derived in any region except E. It also has to be pointed out that the equality of energy formulae is only conjectured in regions D and D'. Consequently, $K_*(\varrho)$ and $L_*(\varrho)$ correspond to $\partial G_m A$ (boundary of the G -closure of the set of effective properties) only in the high-porosity regions A, B, C and A', B', C'. Recall that $K_*(\varrho)$ and $L_*(\varrho)$ are related to $\partial G_m A$ only if optimal stress fields predicted in Sec. 3.1 are statically admissible. In Sec. 4 we prove that this is the case for high-porosity regions. We conjecture the same property for D and D', see the discussion in Sec. 5.

Region A :

$$K_*(\varrho) = \left(\frac{m_1}{K_1 + L_1} + \frac{m_2}{K_2 + L_2} \right)^{-1} - L_2, \quad L_*(\varrho) = L_2. \quad (50)$$

Region A' :

$$K_*(\varrho) = K_2, \quad L_*(\varrho) = \left(\frac{m_1}{K_1 + L_1} + \frac{m_2}{K_2 + L_2} \right)^{-1} - K_2. \quad (51)$$

Region B :

$$\begin{aligned} K_*(\varrho) &= K_2 - \frac{[(1 + \varrho)\sqrt{\varrho m_2} - 2\varrho][1 + \varrho - 2\sqrt{\varrho m_2}]}{2m_1\varrho(1 + \varrho)}(K_1 + L_1), \\ L_*(\varrho) &= \frac{\sqrt{\varrho m_2}(1 + \varrho - 2\sqrt{\varrho m_2})}{2m_1\varrho}(K_1 + L_1) - K_2. \end{aligned} \quad (52)$$

Region B' :

$$\begin{aligned} K_*(\varrho) &= -\frac{\sqrt{-\varrho m_2}(1 - \varrho - 2\sqrt{-\varrho m_2})}{2m_1\varrho}(K_1 + L_1) - L_2, \\ L_*(\varrho) &= L_2 + \frac{[(1 - \varrho)\sqrt{-\varrho m_2} + 2\varrho][1 - \varrho - 2\sqrt{-\varrho m_2}]}{2m_1\varrho(1 - \varrho)}(K_1 + L_1). \end{aligned} \quad (53)$$

Note that $\varrho < 0$ in B'.

Regions C and C' :

$$\begin{aligned} K_*(\varrho) &= \frac{1}{2} \left[(K_2 - L_2) + \frac{(1 - m_2)^2}{m_1(1 + \varrho)}(K_1 + L_1) + \frac{m_2^2 + \varrho}{m_2(1 + \varrho)}(K_2 + L_2) \right], \\ L_*(\varrho) &= \frac{1}{2} \left[\frac{(1 - m_2)^2}{m_1(1 - \varrho)}(K_1 + L_1) + \frac{m_2^2 - \varrho}{m_2(1 - \varrho)}(K_2 + L_2) - (K_2 - L_2) \right]. \end{aligned} \quad (54)$$

Region D :

$$K_*(\varrho) = \left(\frac{m_1}{K_1 + L_1} + \frac{m_2}{K_2 + L_1} \right)^{-1} - L_1, \quad L_*(\varrho) = L_1. \quad (55)$$

Region D' :

$$K_*(\varrho) = K_1, \quad L_*(\varrho) = \left(\frac{m_1}{K_1 + L_1} + \frac{m_2}{K_1 + L_2} \right)^{-1} - K_1. \quad (56)$$

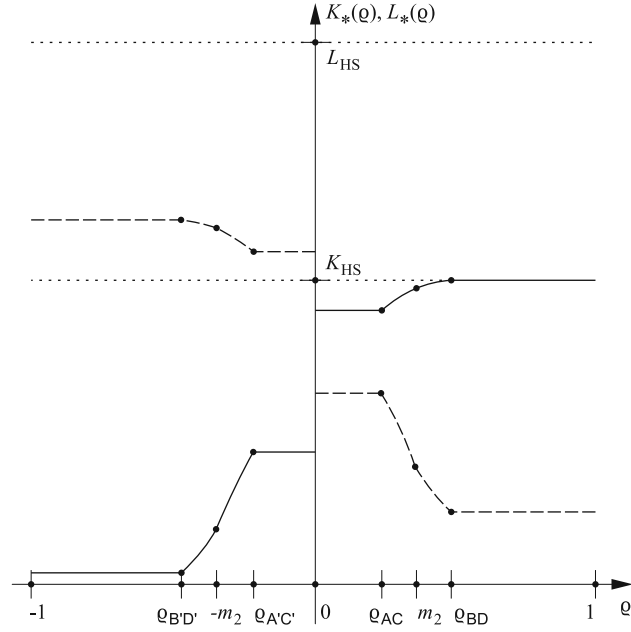


Figure 3: Comparison of optimal bounds $K_*(\varrho)$ (solid lines), $L_*(\varrho)$ (dashed lines) and the Hashin-Shtrikman estimates K_{HS} , L_{HS} (dotted lines). Values of functions are calculated for $m_1 = 0.17$, $m_2 = 0.35$ and $K_1 = 1$, $L_1 = 2$, $K_2 = 3$, $L_2 = 4$. Symbols ϱ_{AC} , ϱ_{BD} , $\varrho_{A'C'}$, $\varrho_{B'D'}$ refer to the anisotropy level of τ_0 at the interfaces between respective regions; $\varrho = 0$ at the interface between A and A', $\varrho = m_2$ at the interface between C and B, $\varrho = -m_2$ at the interface between C' and B'.

Figure 3 illustrates the comparison of functions $K_*(\varrho)$ and $L_*(\varrho)$ representing coupled lower bounds on isotropic properties of a three-phase composite in different regions with the Hashin-Shtrikman uncoupled bounds

$$K_{HS} = \left(\frac{m_1}{K_1 + \alpha_K} + \frac{m_2}{K_2 + \alpha_K} \right)^{-1} - \alpha_K, \quad \alpha_K = L_1,$$

$$L_{HS} = \left(\frac{m_1}{L_1 + \alpha_L} + \frac{m_2}{L_2 + \alpha_L} \right)^{-1} - \alpha_L, \quad \alpha_L = 2K_1 + L_1.$$

Estimates $K_{\text{HS}}, L_{\text{HS}}$ are independent of $\varrho \in [-1, 1]$, as they do not incorporate an information on the anisotropy of τ_0 .

Note that $K_*(\varrho) \leq K_{\text{HS}}$ for all $\varrho \in [-1, 1]$ and $K_*(\varrho) = K_{\text{HS}}$ in region D while the inequality $L_*(\varrho) < L_{\text{HS}}$ is slack in all regions, see the discussion in Sec. 5.1.

4. Optimal high-rank laminates in high-porosity regions

In this Section we show that optimal relaxed stress fields determined in regions A, B, C and A', B', C' coincide with statically admissible stress fields $\tau \in \Sigma$. The task is two-fold. First, we make use of the differential constraint $\text{div}\tau = 0$ in deriving additional requirements on $\tau \in \Sigma_{\text{rel}}$. Next, we show that these requirements are fulfilled in certain microstructures, so-called laminates of high rank.

4.1. Compatibility of stresses on phase interfaces and mean stress fields in rank-one laminates

In calculations of optimal $\tau \in \Sigma_{\text{rel}}$, the differential constraint $\text{div}\tau = 0$ in Y (equilibrium equation) is neglected. Consequently, energy-minimizing stress fields are determined in each phase independently. It follows that components of optimal relaxed fields may be incompatible with $\text{div}\tau = 0$ on material interfaces which in turn means that $\tau \notin \Sigma$.

Suppose that two materials meet in a given microstructure at a line Γ and let n and t denote a normal and tangent to Γ . In the sequel we consider microstructures where phases are arranged in layers hence Γ takes a form of a straight line. Moreover, we assume that stress field in each layer is constant. By this we claim that if a given non-degenerate phase $Y_i, i = 1, 2$, is distributed in p layers $Y_{i,1}, Y_{i,2}, \dots, Y_{i,p}$, then optimal τ is *layer-wise constant* in Y_i . It follows that if $p = 1$ then τ is constant in entire Y_i . Equilibrium equation is thus fulfilled identically in each phase.

Constraint $\text{div}\tau = 0$ requires that $[[\tau n]]_{\Gamma} = 0$ where $[[\cdot]]_{\Gamma}$ denotes a jump on the interface Γ between layers of materials. If we set $\tau_m, m = 1, 2$, for constant fields on both sides of Γ then the jump condition may be rewritten in a form

$$(\tau_1 - \tau_2) : (n \otimes n) = (\tau_1 - \tau_2) : (n \otimes t) = (\tau_1 - \tau_2) : (t \otimes n) = 0.$$

It follows that stress fields with $(\tau_1 - \tau_2) : (t \otimes t) \neq 0$ are compatible with the equilibrium constraint hence statically admissible in Y , see (Cherkaev, 2000, Sec. 14.2.2) for full discussion of this topic.

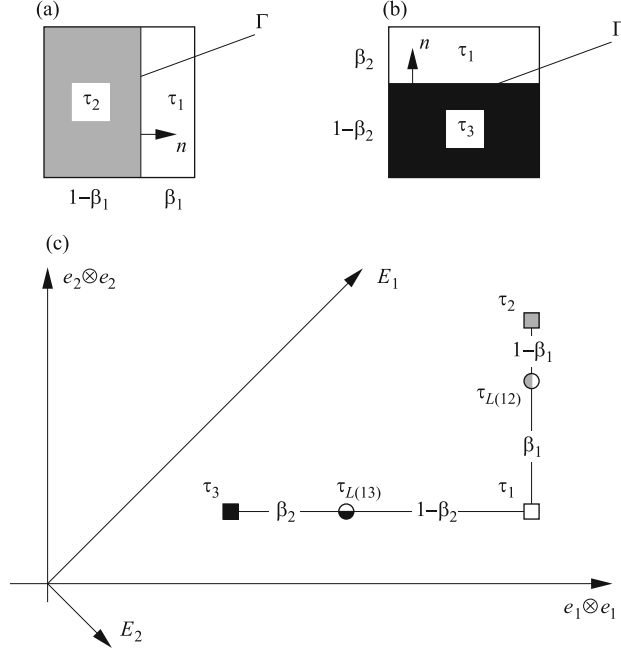


Figure 4: Rank-one connectivity of stress fields τ_m , $m = 1, 2, 3$ such that $\tau_m : (e_1 \otimes e_2) = 0$: (a) simple laminate $L(12)$ with phases taken in proportions β_1 , $1 - \beta_1$, a normal to the interface Γ given by $n = e_1$ and stress fields τ_1 and τ_2 ; (b) simple laminate $L(13)$ with phases taken in proportions β_2 , $1 - \beta_2$, a normal to the interface Γ given by $n = e_2$ and constant stress fields τ_1 and τ_3 ; (c) graphical interpretation of compatibility conditions $(\tau_1 - \tau_2) : (e_1 \otimes e_1) = 0$, $(\tau_1 - \tau_3) : (e_2 \otimes e_2) = 0$ and mean fields $\tau_{L(12)}$ in laminate $L(12)$, $\tau_{L(13)}$ in laminate $L(13)$. Vectors E_1 , E_2 are defined in (2).

Here we discuss stresses τ_1 , τ_2 in two materials arranged in a rank-one laminate $L(12)$. Compatibility of stress fields in $L(12)$ is also referred to as *rank-one connectivity at Γ* . Let τ_1 and τ_2 denote rank-one connected stress fields in materials layered in proportions β and $1 - \beta$ respectively. Resulting mean field takes a value $\tau_{L(12)} = \beta \tau_1 + (1 - \beta) \tau_2$. Examples of rank-one connected stress fields and their mean values in simple laminates are sketched in Fig. 4. High-rank laminates are constructed by repeated rank-one layering scheme under the assumption that the materials resulting from previous laminations are homogeneous. These type of structures are considered in the subsequent section.

4.2. Stress fields in microstructures

4.2.1. Regions C and C'

Region C : Continuing the discussion in Sec. 3.2.1 one may notice that the assumption $S_1 = D_{11}$ enforces $\theta(y) = 0$ a.e. in Y_1 . Consequently, optimal stress field $\tau \in \Sigma_{\text{rel}}$ is constant in Y_1 . We thus calculate

$$\begin{aligned}\tau_1 &= \frac{1 - m_2}{m_1} e_1 \otimes e_1 && \text{a.e. in } Y_1, \\ \tau_2 &= 1 e_1 \otimes e_1 + \frac{\varrho}{m_2} e_2 \otimes e_2 && \text{a.e. in } Y_2.\end{aligned}\tag{57}$$

In order to prove statical admissibility of (57) we check the compatibility of stresses on material interfaces in a $L(13, 2)$ laminate, see Fig. 5.

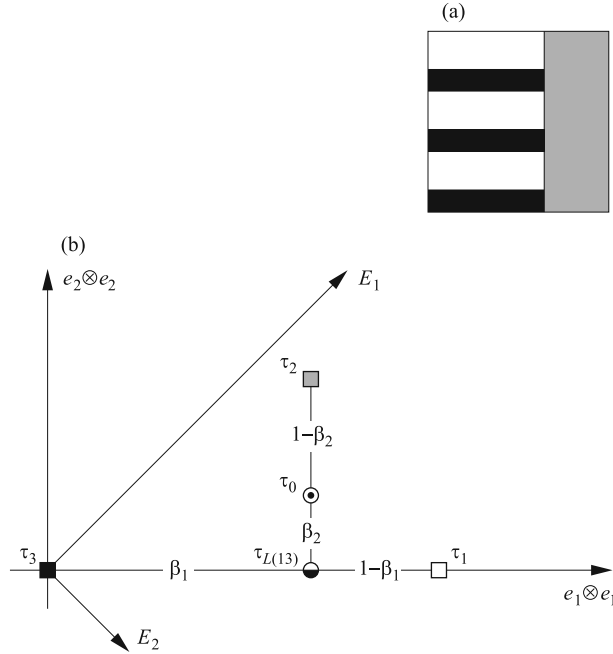


Figure 5: Optimal microstructure in regions C and C': (a) layout of materials; (b) layering scheme leading to $\tau_0 = \tau_{L(13,2)}$ for region C (a mirror image with respect to $e_1 \otimes e_1$ results in the scheme for region C'). Stress fields in layers of strong and weak materials are represented by white and grey squares respectively, $\tau = 0$ in void is represented by black square. Circles represent stress fields in laminates.

Outline of the layering scheme:

1. Substructure $L(13)$ is formed: phase 1 and void are laminated with $n_1 = e_2$ and volume fractions $\beta_1, 1 - \beta_1$ respectively. Homogenized stress field in $L(13)$ is given by $\tau_{L(13)} = \beta_1 \tau_1$.
2. Final structure $L(13, 2)$ is formed: phase 2 and $L(13)$ are laminated with $n_2 = e_1$ and volume fractions $\beta_2, 1 - \beta_2$ respectively. Fields $\tau_{L(13)}$ and τ_2 are rank-one connected if $(\tau_{L(13)} - \tau_2) : (e_1 \otimes e_1) = 0$. Stress field in the final structure $\tau_{L(13,2)} = \beta_2 \tau_2 + (1 - \beta_2) \tau_{L(13)}$ satisfies $\tau_{L(13,2)} = \tau_0$.

Parameters of optimal laminate: Compatibility conditions reduce to

$$\begin{aligned} \tau_{L(13)} : (e_1 \otimes e_1) = 1 &\Rightarrow \beta_1 = \frac{m_1}{1 - m_2} \in [0, 1], \\ \tau_{L(13,2)} : (e_2 \otimes e_2) = \varrho &\Rightarrow \beta_2 = m_2 \in [0, 1] \end{aligned} \quad (58)$$

and it is immediate that the constraints on volume fractions of phases in Y given by

$$\beta_1(1 - \beta_2) = m_1, \quad \beta_2 = m_2$$

are satisfied identically.

Region C' : In addition to the considerations in Sec. 3.2.3 and due to assumed $S_1 = D_{11}$ we set $s(y) = d_1(y) = S_1$ a.e. in Y_1 . Further discussion reduces to the one presented above with $\varrho \in [-1, 0]$ taken into account. Spherical and deviatoric components of mean stress in each phase are given by the same formulae in both regions C and C' , see (31) and (40). Consequently, stress field in laminate $L(13, 2)$ fulfills the sufficient condition of optimality also in region C' with phase volume fractions given by (58). Layout of materials and scheme of layering corresponding to region C' are sketched in Fig. 5.

4.2.2. Regions B and B'

Region B : Here we continue the discussion in Sec. 3.2.1 with the assumption $D_{11} < S_1$. Function $\theta(y)$, $y \in Y_1$, may vary in Y_1 hence the stress field in material 1 are rank-one connected with zero stress in void if $\theta(y) = 0$ or $\theta(y) = \pi$. Taking this into consideration we subdivide phase 1 into two

layers, i.e. we set $Y_1 = Y_{1,1} + Y_{1,2}$. Formulae for stresses read

$$\begin{aligned}\tau_{1,1} &= \frac{1 + \varrho - 2\sqrt{\varrho m_2}}{m_1} e_1 \otimes e_1 \quad \text{a.e. in } Y_{1,1}, \\ \tau_{1,2} &= \frac{1 + \varrho - 2\sqrt{\varrho m_2}}{m_1} e_2 \otimes e_2 \quad \text{a.e. in } Y_{1,2}, \\ \tau_2 &= \frac{\sqrt{\varrho m_2}}{m_2} (e_1 \otimes e_1 + e_2 \otimes e_2) \quad \text{a.e. in } Y_2.\end{aligned}\tag{59}$$

Next, we prove statical admissibility of (59) by checking rank-one connectivity of stress fields in a $L(13_1, 2, 13_2)$ laminate, see Fig. 6.

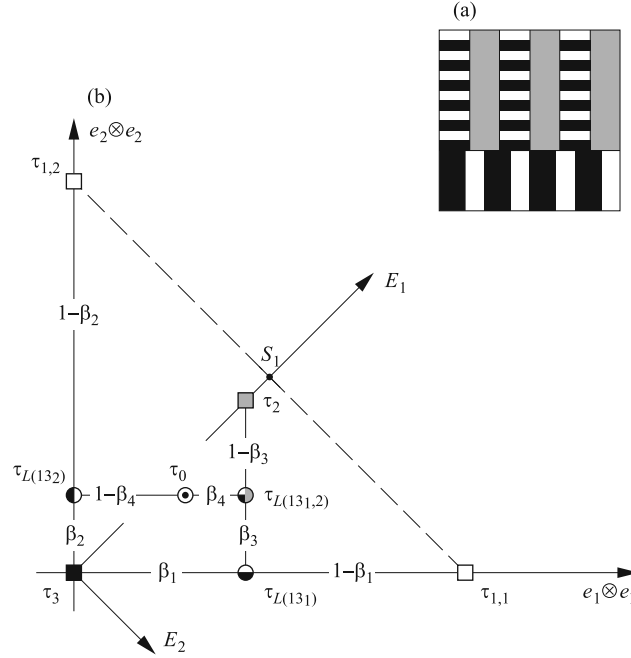


Figure 6: Optimal microstructure in regions **B** and **B'**: (a) layout of materials; (b) layering scheme leading to $\tau_0 = \tau_{L(13_1,2,13_2)}$ for region **B** (a mirror image with respect to $e_1 \otimes e_1$ results in the scheme for region **B'**). Stress fields in layers of strong and weak materials are represented by white and grey squares respectively, $\tau = 0$ in void is represented by black square. Circles represent stress fields in laminates.

Outline of the layering scheme:

1. Substructures $L(13_1)$ and $L(13_2)$ are formed. In $L(13_1)$, the first layer of phase 1 (field $\tau_{1,1}$) and void are laminated with $n_1 = e_2$ and volume

fractions $\beta_1, 1 - \beta_1$ respectively. Stress field in $L(13_1)$ is given by $\tau_{L(13_1)} = \beta_1 \tau_{1,1}$. In $L(13_2)$, the second layer of phase 1 (field $\tau_{1,2}$) and void are laminated with $n_2 = e_1$ and volume fractions $\beta_2, 1 - \beta_2$. Stress field in $L(13_2)$ reads $\tau_{L(13_2)} = \beta_2 \tau_{1,2}$.

2. Substructure $L(13_1, 2)$ is formed: phase 2 and $L(13_1)$ are laminated with $n_3 = e_1$ and volume fractions $\beta_3, 1 - \beta_3$. Fields $\tau_{L(13_1)}$ and τ_2 are rank-one connected if $(\tau_{L(13_1)} - \tau_2) : (e_1 \otimes e_1) = 0$. Stress field in the substructure is given by $\tau_{L(13_1,2)} = \beta_3 \tau_2 + (1 - \beta_3) \tau_{L(13_1)}$.
3. Final structure $L(13_1, 2, 13_2)$ is formed: laminates $L(13_2)$ and $L(13_1, 2)$ are layered with $n_4 = e_2$ and volume fractions β_4 and $1 - \beta_4$. Rank-one connection between stress fields holds if $(\tau_{L(13_2)} - \tau_{L(13_1,2)}) : (e_2 \otimes e_2) = 0$. Formulae $\tau_{L(13_1,2,13_2)} = \beta_4 \tau_{0,2} + (1 - \beta_4) \tau_{0,3}$ and $\tau_{L(13_1,2,13_2)} = \tau_0$ link the fields in substructures with the effective stress tensor.

Parameters of optimal laminate: Collecting the compatibility conditions we get the following

$$\begin{aligned}
(\tau_{L(13_1)} - \tau_2) : (e_1 \otimes e_1) = 0 & \Rightarrow \beta_1 = \frac{S_2}{2S_1}, \\
(\tau_{L(13_2)} - \tau_{L(13_1,2)}) : (e_2 \otimes e_2) = 0 & \Rightarrow \beta_2 = \frac{\beta_3 S_2}{2S_1}, \\
\tau_{L(13_1,2,13_2)} : (e_2 \otimes e_2) = \varrho & \Rightarrow \beta_3 = \frac{\sqrt{2} \varrho}{S_2}, \\
\tau_{L(13_1,2,13_2)} : (e_1 \otimes e_1) = 1 & \Rightarrow \beta_4 = 1 - \frac{\sqrt{2}}{S_2}.
\end{aligned}$$

Parameters $\beta_i \in [0, 1]$, $i = 1, \dots, 4$, as $\sqrt{2} \leq S_2 \leq S_1$ in entire region **B**. Indeed, it is a matter of straightforward calculations to check that the first inequality immediately follows due to $\varrho \geq m_2$ in **B** and the second one reduces to

$$m_1 \leq \psi_{\mathbf{B-D}}(\varrho, m_2) \frac{K_1 + L_2}{K_1 + L_1}$$

by substituting relevant formulae from (28) and (29).

Constraints on volume fractions of phases in Y are satisfied if $|Y_{1,1}| + |Y_{1,2}| = m_1$ and $|Y_2| = m_2$ or, equivalently,

$$\begin{aligned}
(1 - \beta_3)(1 - \beta_4)\beta_1 + \beta_4 \beta_2 &= m_1, \\
(1 - \beta_4)\beta_3 &= m_2
\end{aligned}$$

from which we have

$$\begin{aligned}\beta_1 &= \frac{m_1 \sqrt{\varrho m_2}}{m_2(1 + \varrho - 2\sqrt{\varrho m_2})}, \quad \beta_2 = \frac{m_1 \varrho}{1 + \varrho - 2\sqrt{\varrho m_2}}, \\ \beta_3 &= \sqrt{\varrho m_2}, \quad \beta_4 = 1 - \sqrt{\frac{m_2}{\varrho}}.\end{aligned}\tag{60}$$

Note that $L(13_1, 2, 13_2)$ (optimal in region **B**) morphs into $L(13, 2)$ (optimal in **C**) at the boundary between regions. This is concluded by setting $\varrho = m_2$ in $\beta_1, \dots, \beta_4$ above.

Region B' : From the discussion in Sec. 3.2.3 and the assumption that $S_1 < D_{11}$ it follows that phase 1 is subdivided into two layers such that $Y_1 = Y_{1,1} + Y_{1,2}$ with $s(y) = D_{11}$ a.e. in $Y_{1,1}$ and $s(y) = -D_{11}$ a.e. in $Y_{1,2}$. In this way, stress fields are given by

$$\begin{aligned}\tau_{1,1} &= \frac{1 - \varrho - 2\sqrt{-\varrho m_2}}{m_1} e_1 \otimes e_1 \quad \text{a.e. in } Y_{1,1}, \\ \tau_{1,2} &= -\frac{1 - \varrho - 2\sqrt{-\varrho m_2}}{m_1} e_2 \otimes e_2 \quad \text{a.e. in } Y_{1,2}, \\ \tau_2 &= \frac{\sqrt{-\varrho m_2}}{m_2} (e_1 \otimes e_1 - e_2 \otimes e_2) \quad \text{a.e. in } Y_2.\end{aligned}$$

Thus described stress field in laminate $L(13_1, 2, 13_2)$ is statically admissible in region **B'**. Phase volume fractions are given by (60) with ϱ replaced with $-\varrho$. The details of calculations are omitted here as they follow the same pattern as presented above. Layout of materials and scheme of layering corresponding to region **B'** are sketched in Fig. 6.

4.2.3. Regions A and A'


Region **A** splits into two subregions A_1, A_2 with different optimal microstructures.

Subregion A_1 : We use the results of Sec. 3.2.2 to prove that the stress fields

$$\begin{aligned}\tau_1 &= \sqrt{2} S_1 e_1 \otimes e_1 \quad \text{a.e. in } Y_1, \\ \tau_{2,1} &= \sqrt{2} S_2 e_1 \otimes e_1 \quad \text{a.e. in } Y_{2,1}, \\ \tau_{2,2} &= \frac{S_2 + f_1}{\sqrt{2}} e_1 \otimes e_1 + \frac{S_2 - f_1}{\sqrt{2}} e_2 \otimes e_2 \quad \text{a.e. in } Y_{2,2}\end{aligned}$$

(a)

The diagram shows a vertical stack of seven horizontal layers on the left. From top to bottom, the layers are: white, gray, black, white, gray, black, and gray. To the right of this stack is a large, solid gray rectangular region.

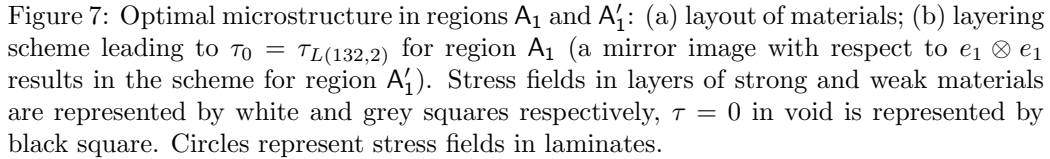

1. Substructure $L(123)$ is formed in two steps: (i) phase 1 and void are layered with $n_1 = e_2$ and volume fractions β_1 and $1 - \beta_1$ (in this way $L(13)$ with $\tau_{0,1} = \beta_1 \tau_1$ is obtained), (ii) first layer of phase 2 and $L(13)$ are laminated in the same direction with volume fractions β_2 and $1 - \beta_2$; this leads to $L(123)$ with $\tau_{L(123)} = \beta_2 \tau_{2,1} + (1 - \beta_2) \beta_1 \tau_1$.
2. Final structure $L(123, 2)$ is formed: second layer of phase 2 (field $\tau_{2,2}$) and $L(123)$ are laminated with $n_3 = e_1$ and volume fractions β_3 and $1 - \beta_3$. Rank-one connectivity requirement reads $(\tau_{L(123)} - \tau_{2,2}) : (e_1 \otimes$

$e_1) = 0$. Stress field $\tau_{L(123,2)} = \beta_3 \tau_{2,2} + (1 - \beta_3) \tau_{L(123)}$ matches the effective tensor by $\tau_{L(123,2)} = \tau_0$.

Parameters of optimal laminate: Rank-one connectivity requirements simplify to

$$\begin{aligned} (\tau_{L(123)} - \tau_{2,2}) : (e_1 \otimes e_1) = 0 &\Rightarrow \beta_1 = \frac{1}{(1 - \beta_2)S_1} \left(\frac{1}{\sqrt{2}} - \beta_2 S_1 \right), \\ \tau_{L(123,2)} : (e_2 \otimes e_2) = \varrho &\Rightarrow \beta_3 = \frac{\varrho}{\sqrt{2}S_2 - 1} \end{aligned}$$

and constraints on volume fractions in Y are fulfilled if $|Y_1| = m_1$ and $|Y_{2,1}| + |Y_{2,2}| = m_2$, i.e.

$$(1 - \beta_2)(1 - \beta_3)\beta_1 = m_1, \quad (1 - \beta_3)\beta_2 + \beta_3 = m_2.$$

Therefore, optimal laminate is parameterized by

$$\begin{aligned} \beta_1 &= \frac{m_1}{1 - m_2}, & \beta_2 &= \frac{m_2(1 - m_2)\kappa - m_1(m_2 + \varrho)}{(1 + \varrho)[(1 - m_2)\kappa - m_1]}, \\ \beta_3 &= \frac{\varrho(m_1 + m_2\kappa)}{(1 + \varrho - m_2)\kappa - m_1}, & \kappa &= \frac{K_1 + L_1}{K_2 + L_2}. \end{aligned} \quad (61)$$

Note that $\kappa \in [0, 1]$.

Our next claim is that $\beta_i \in [0, 1]$, $i = 1, 2, 3$. Indeed, β_1 coincides with that in region **C** and the remaining conditions can be reduced to

$$\begin{aligned} \beta_2 &\geq 0 && \text{if } m_1 \leq \psi_{\mathbf{A-C}}(m_2, \varrho), \\ \beta_2 &\leq 1 \text{ and } \beta_3 &\geq 0 &\text{if } m_1 \leq (1 + \varrho - m_2)\kappa, \\ \beta_3 &\leq 1 && \text{if } m_1 \leq (1 - m_2)\kappa. \end{aligned} \quad (62)$$

For the definition of $\psi_{\mathbf{A-C}}(m_2, \varrho)$ and $\psi_{\mathbf{A-B}}(m_2, \varrho)$ (used below) see Sec. 3.2.1. It follows that the first constraint in (62) is most restrictive. Hence, $\mathbf{A} = \mathbf{A}_1 \cup \mathbf{A}_2$ where

$$\begin{aligned} \mathbf{A}_1 &= \left\{ (m_1, \varrho) : 0 \leq m_1 \leq \psi_{\mathbf{A-C}}(m_2, \varrho), \varrho \in [0, 1] \right\}, \\ \mathbf{A}_2 &= \left\{ (m_1, \varrho) : \psi_{\mathbf{A-C}}(m_2, \varrho) \leq m_1 \leq \psi_{\mathbf{A-B}}(m_2, \varrho), \varrho \in [m_2, 1] \right\}. \end{aligned}$$

Laminate $L(123, 2)$ (optimal in $\mathbf{A}_1$) morphs into $L(13, 2)$ (optimal in **C**) at the boundary between regions. This follows from substituting $m_1 = \psi_{\mathbf{A-C}}(m_2, \varrho)$ in β_2 and β_3 .

Subregion A_2 : We make use of “the coating principle”, see (Albin et al., 2007, Th. 9), in determining optimal microstructure in subregion A_2 . Laminate $L(13_1, 2, 13_2)$ (optimal in region B) is coated with a layer of phase 2, in the direction $n_5 = e_1$ normal to the interface, and volume fractions $1 - \beta_5$ and β_5 . In this way, $L(13_1, 2, 13_2, 2)$ is obtained. Phases 1 and 2 are thus subdivided according to $Y_1 = Y_{1,1} + Y_{1,2}$ and $Y_2 = Y_{2,1} + Y_{2,2}$ respectively. Formulae for stress fields in phases read

$$\begin{aligned}
\tau_{1,1} &= \sqrt{2} S_1 e_1 \otimes e_1 && \text{a.e. in } Y_{1,1}, \\
\tau_{1,2} &= \sqrt{2} S_1 e_2 \otimes e_2 && \text{a.e. in } Y_{1,2}, \\
\tau_{2,1} &= \frac{S_2}{\sqrt{2}} (e_1 \otimes e_1 + e_2 \otimes e_2) && \text{a.e. in } Y_{2,1}, \\
\tau_{2,2} &= \frac{S_2 + f_2}{\sqrt{2}} e_1 \otimes e_1 + \frac{S_2 - f_2}{\sqrt{2}} e_2 \otimes e_2 && \text{a.e. in } Y_{2,2}.
\end{aligned} \tag{63}$$

Technically, sufficient condition of optimality in subregion A_2 do not restrict stress field in $Y_{2,1}$ to be spherical. However, the assumed form of $\tau_{2,1}$ proves to be optimal as it is shown in the sequel. We also assume $\tau_{2,2} : (e_1 \otimes e_1) = 1$ which gives $f_2 = \sqrt{2} - S_2$ in (63).

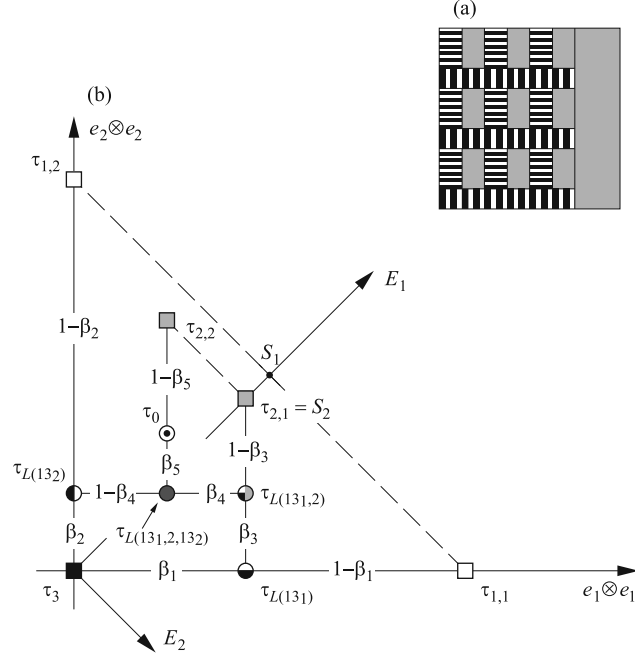


Figure 8: Optimal microstructure in regions A_2 and A'_2 : (a) layout of materials; (b) layering scheme leading to $\tau_0 = \tau_{L(131,2,132,2)}$ for region A_2 (a mirror image with respect to $e_1 \otimes e_1$ results in the scheme for region A'_2). Stress fields in layers of strong and weak materials are represented by white and grey squares respectively, $\tau = 0$ in void is represented by black square. Circles represent stress fields in laminates.

Outline of the layering scheme:

1. Substructure $L(13_1, 2, 13_2)$ is formed along the scheme discussed in case of region B hence it is not repeated here.
2. Final structure $L(13_1, 2, 13_2, 2)$ is formed: second layer of phase 2 (field $\tau_{2,2}$) and $L(13_1, 2, 13_2)$ are laminated with $n_5 = e_1$ and volume fractions $1 - \beta_5$ and β_5 . Rank-one connectivity condition is given by $(\tau_{L(13_1,2,13_2)} - \tau_{2,2}) : (e_1 \otimes e_1) = 0$. Stress field in $L(13_1, 2, 13_2, 2)$ is linked to the effective tensor by $\tau_{L(13_1,2,13_2,2)} = \beta_5 \tau_{2,2} + (1 - \beta_5) \tau_{0,4}$ and $\tau_{L(13_1,2,13_2,2)} = \tau_0$.

Parameters of optimal laminate: Rank-one compatibility of stress fields in

substructures and resulting relations between laminate parameters read

$$\begin{aligned}
(\tau_{L(13_1)} - \tau_{2,1}) : (e_1 \otimes e_1) &= 0 \quad \Rightarrow \quad \beta_1 = \frac{S_2}{2 S_1}, \\
(\tau_{L(13_2)} - \tau_{L(13_1,2)}) : (e_2 \otimes e_2) &= 0 \quad \Rightarrow \quad \beta_2 = \frac{\beta_3 S_2}{2 S_1}, \\
(\tau_{L(13_1,2,13_2)} - \tau_{2,2}) : (e_1 \otimes e_1) &= 0 \quad \Rightarrow \quad \beta_4 = 1 - \frac{\sqrt{2}}{S_2}
\end{aligned} \tag{64}$$

and the constraints on volume fractions are given by $|Y_{1,1}| + |Y_{1,2}| = m_1$ and $|Y_{2,1}| + |Y_{2,2}| = m_2$, or explicitly

$$\begin{aligned}
(1 - \beta_5) [(1 - \beta_4)(1 - \beta_3)\beta_1 + \beta_4 \beta_2] &= m_1, \\
(1 - \beta_5)(1 - \beta_4)\beta_3 + \beta_5 &= m_2.
\end{aligned}$$

Introducing

$$x = \kappa (1 + \varrho) > 0, \quad y = 2 (m_1 + m_2 \kappa) > 0, \quad x \geq y \tag{65}$$

gives

$$\begin{aligned}
\beta_3 &= \frac{x [(m_2 + \varrho)y - 2 m_2 x]}{(x - y)^2 (1 - \beta_5)}, \\
\beta_5 &= \frac{m_2 x^2 - \varrho y^2}{(x - y)^2}.
\end{aligned} \tag{66}$$

and we proceed to show that $\beta_i \in [0, 1]$, $i = 1, \dots, 5$.

From $\kappa \in [0, 1]$ it follows that β_1 fulfills the condition. Parameter β_4 falls into required interval if $S_2 \geq \sqrt{2}$ in subregion $\mathbf{A}_2$. This condition is satisfied if $2 m_1 \leq (1 + \varrho - 2 m_2)\kappa$. Observe that

$$m_1 \leq \psi_{\mathbf{A-B}}(m_2, \varrho) \leq \frac{(1 + \varrho - 2 m_2)\kappa}{2}$$

holds for $m_2 \leq \varrho$. Thus $\beta_4 \in [0, 1]$.

We can assert that $\beta_5 \geq 0$ if $m_2 x^2 - \varrho y^2 \geq 0$. This inequality can be reformulated to $m_1 \leq \psi_{\mathbf{A-B}}(m_2, \varrho)$ and the assertion follows. In order to prove $\beta_5 \leq 1$ we show that

$$(x - y)^2 - m_2 x^2 + \varrho y^2 \geq 0 \tag{67}$$

in entire A_2 . To this end, we first rewrite (67) in the form

$$\begin{aligned} (1 + \varrho)(y - y_1)(y - y_2) &\geq 0, \\ y_{1,2} &= \left(1 \pm \sqrt{(1 + \varrho)m_2 - \varrho}\right) \kappa, \quad y_1 \geq y_2, \end{aligned} \quad (68)$$

and the proof falls naturally into two parts. If $(1 + \varrho)m_2 - \varrho < 0$ then the roots in (68) do not exist and (67) follows immediately.

Conversely, let us assume that $(1 + \varrho)m_2 - \varrho \geq 0$. Next, make use of (65) and (68) to calculate

$$m_y(m_2, \varrho) = \frac{1 - 2m_2 + \sqrt{(1 + \varrho)m_2 - \varrho}}{2} \kappa$$

where m_y represents values of m_1 corresponding to y_1 . To show that (67) holds it is sufficient to check if $m_y(m_2, \varrho) < \psi_{A-C}(m_2, \varrho)$. The latter is fulfilled if $(1 + \varrho)m_2 - \varrho \geq -m_2$ which may be concluded from the assumption.

Comparing the expressions in (66) we deduce that the discussion of $\beta_3 \geq 0$ may be reduced to proving $(m_2 + \varrho)y - 2m_2x \geq 0$. It is straightforward to compute that this inequality is equivalent to $m_1 \geq \psi_{A-C}(m_2, \varrho)$. For checking if $\beta_3 \leq 1$ we write it in a form $(x - y)[x(1 + m_2) - y(1 + \varrho)] \geq 0$. From (65) we see that it suffices to show that $x(1 + m_2) - y(1 + \varrho) \geq 0$. This requirement reduces to $2m_1 \leq (1 - m_2)\kappa$ which is valid in entire A_2 due to

$$m_1 \leq \psi_{A-B}(m_2, \varrho) \leq \frac{(1 - m_2)\kappa}{2}.$$

The property of $\beta_2 \in [0, 1]$ follows from $\beta_3 \in [0, 1]$, see (64).

Recall that a boundary between regions A_1 and A_2 is given by $m_1 = \psi_{A-C}(m_2, \varrho)$, $\varrho \geq m_2$. By substituting this formula in $\beta_1, \dots, \beta_5$ one may check that $L(13_1, 2, 13_2, 2)$ (optimal in A_2) morphs into $L(123, 2)$ (optimal in A_1). By the same token, setting $m_1 = \psi_{A-B}(m_2, \varrho)$ in $\beta_1, \dots, \beta_5$ leads to the conclusion that $L(13_1, 2, 13_2, 2)$ smoothly changes into $L(13_1, 2, 13_2)$ (optimal in B).

Similarly to A, region A' also splits into A_1' and A_2' . Optimal microstructures in both subregions are the same as in A_1 and A_2 respectively.

Subregion A_1' : For proving optimality of the laminate $L(123, 2)$ we make use of the results obtained in Sec. 3.2.4. Stress fields in phases read

$$\begin{aligned}\tau_1 &= \sqrt{2} D_{11} e_1 \otimes e_1 && \text{a.e. in } Y_1, \\ \tau_{2,1} &= \sqrt{2} D_{21} e_1 \otimes e_1 && \text{a.e. in } Y_{2,1}, \\ \tau_{2,2} &= \frac{g_1 + D_{21}}{\sqrt{2}} e_1 \otimes e_1 + \frac{g_1 - D_{21}}{\sqrt{2}} e_2 \otimes e_2 && \text{a.e. in } Y_{2,2}\end{aligned}$$

where D_{11} , D_{21} are given by (44). We assume that $\tau_{2,2} : (e_1 \otimes e_1) = 1$ from which it follows that $g_1 = \sqrt{2} - D_{21}$. Further calculations are similar to those presented for subregion A_1 . They lead to formulae for optimal lamination parameters written in (61) with ϱ replaced by $-\varrho$.

Subregion A_2' : Laminate $L(13_1, 2, 13_2, 2)$ proves to be optimal also in subregion A_2' . Stress fields are given by

$$\begin{aligned}\tau_{1,1} &= \sqrt{2} D_{11} e_1 \otimes e_1 && \text{a.e. in } Y_{1,1}, \\ \tau_{1,2} &= \sqrt{2} D_{11} e_2 \otimes e_2 && \text{a.e. in } Y_{1,2}, \\ \tau_{2,1} &= \frac{D_{21}}{\sqrt{2}} (e_1 \otimes e_1 - e_2 \otimes e_2) && \text{a.e. in } Y_{2,1}, \\ \tau_{2,2} &= \frac{g_2 + D_{21}}{\sqrt{2}} e_1 \otimes e_1 + \frac{g_2 - D_{21}}{\sqrt{2}} e_2 \otimes e_2 && \text{a.e. in } Y_{2,2}\end{aligned}$$

and we assume that $\tau_{2,2} : (e_1 \otimes e_1) = 1$ hence $g_2 = \sqrt{2} - D_{21}$. Optimal lamination parameters are derived similarly to those in region A_2 . They read

$$\begin{aligned}\beta_1 &= \frac{D_{21}}{2 D_{11}}, & \beta_2 &= \frac{D_{21} \beta_3}{2 D_{11}}, \\ \beta_3 &= \frac{x' [(m_2 - \varrho)y' - 2 m_2 x']}{(x' - y')^2 (1 - \beta_5)}, & \beta_4 &= 1 - \frac{\sqrt{2}}{D_{21}}, \\ \beta_5 &= \frac{m_2 (x')^2 + \varrho (y')^2}{(x' - y')^2}\end{aligned}$$

where $x' = (1 - \varrho) \kappa$ and $y' = y$.

Proof of $\beta_i \in [0, 1]$, $i = 1, \dots, 5$ in subregion A_2' follows the pattern set in the discussion regarding A_2 .

5. Final remarks

5.1. Remarks on low-porosity regions D, D' and E

The detailed description of the mentioned regions D , D' and E of large volume fraction of the first material, or, equivalently, low-porosity regions,

will be provided in a separate paper. Here we restrict ourselves with some brief remarks outlining the current results.

Region D: The Hashin-Shtrikman bound on bulk modulus At the boundary of regions B and C that correspond to maximal allowed volume fraction m_1 , the optimal translation parameter reaches the value of L_1 . The energy bound $U_{\text{tr}}(\varrho)$ in region B transforms into the classical translation bound which corresponds to the Hashin - Shtrikman bound on the bulk modulus for isotropic composites. This bound is realizable, see (Cherkaev, 2009, 2012). The anisotropic translation bound is attained on certain microstructures only when the anisotropy level is not too large, compare the discussion in (Cherkaev and Zhang, 2011). The optimal structures for both conducting and elastic composites are similar, they are determined by high-rank orthogonal laminates $L(13_1, 2, 13_2, 1, 1)$. These structures are obtained by enveloping the nucleus laminate $L(13_1, 2, 13_2)$ - optimal for the region B - by two orthogonal layers of the first material. It is shown in (Albin et al., 2007) that such enveloping is stable with respect to the translation bound: if the nucleus satisfies this bound, then the enveloped nucleus also satisfies it.

Region D': Similarly, at the boundary of regions B' and C', the optimal translation parameter reaches the value of $-K_1$. However, in this case, the energy bound $U_{\text{tr}}(\varrho)$ in region B' *does not* give rise to the Hashin - Shtrikman bound on the shear modulus for isotropic composites.

Indeed, U_{tr} measures the energy of a composite subjected to an arbitrary stress field whose anisotropy is controlled by $\varrho \in [-1, 1]$. Consequently, if we set $\varrho = 1$ then the effective energy is optimized only in a direction of the applied field $\tau_0 = [(1 + \varrho)/2] E_1$ which is spherical, i.e. isotropic.

On the contrary, setting $\varrho = -1$ does not lead to a similar conclusion because applying the deviatoric field $\tau_0 = [(1 - \varrho)/2] E_2$ and retaining the isotropy of a composite medium by controlling its response in the direction E_3 at the same time is impossible.

Region E: Guessed optimal structures Optimal $L(13_1, 2, 13_2, 1, 1)$ structures degenerate into the most anisotropic $L(13, 2, 1)$, when the anisotropy of the external field increases (the value of ϱ decreases from 1 towards 0). When the anisotropy level increases even further, the translation

bound is not realizable by the known structures. Moreover, it is definitely not optimal for strongly anisotropic structures; the reasons are discussed in (Cherkaev and Zhang, 2011).

We conjecture that the region **E** of large volume fractions m_1 and strongly anisotropic loadings correspond to the limiting structures $L(13, 2, 1)$. The bound for this region is presently unknown, and we guess that it corresponds to another inequality that becomes an equality in that region. To support our guess we mention that:

- the optimal structure in Region **C** is $L(13, 2)$. The $L(13, 2, 1)$ structures degenerate into them, when the fraction of external layer of the first material vanishes;
- the best known bounds for extremely anisotropic structures ($\varrho \rightarrow 0$) correspond to the same structure $L(13, 2, 1)$ in that region, see (Cherkaev and Gibiansky, 1996);
- the structures that realize the translation bound for moderately anisotropic loadings, also degenerate into $L(13, 2, 1)$;
- the $L(13, 2, 1)$ structures degenerate into $L(13)$ when the fraction of the second material disappears;
- the $L(13, 2, 1)$ structures degenerate into $L(12)$ when the fraction of the third material (void) disappears.

In the absence of the bound, one cannot prove the sufficient optimality conditions for the guessed structures and therefore the global character of their optimality. It can be numerically shown, however, that the relative gap between a rough bound for the energy and a structure of this class is very small, see (Cherkaev and Zhang, 2011). Therefore, these structures are either optimal or a close approximation of optimal, and can be treated as optimal for practical purposes.

Acknowledgements

This work has been partially supported by the European Union in the framework of European Social Fund through the Warsaw University of Technology Development Programme (Grzegorz Dzierżanowski).

References

- Albin, N., Cherkaev, A., Nesi, V., 2007. Multiphase laminates of extremal effective conductivity in two dimensions. *J. Mech. Phys. Solids* 55(7), 1513–1553.
- Alessandrini, G., Nesi, V., 2001. Univalent σ -harmonic mappings. *Arch. Rat. Mech. Anal.* 158(2), 155–171.
- Allaire, G., 2002. *Shape Optimization by the Homogenization Method*. Springer, New York.
- Bendsøe, M.P., Sigmund, O., 2003. *Topology Optimization. Theory, Methods and Applications*. Springer, Berlin Heidelberg.
- Bergman, D.J., 1978. The dielectric constant of a composite material - A problem in classical physics. *Phys. Rep.* 43(9), 377-407.
- Cherkaev, A.V., 2000. *Variational Methods for Structural Optimization*. Springer, New York.
- Cherkaev, A., 2009. Bounds for effective properties of multimaterial two-dimensional conducting composites. *Mech. Mater.* 41(4), 411-433.
- Cherkaev, A., 2012. Optimal three-material wheel assemblage of conducting and elastic composites. *Int. J. Engrg. Sci.* 59, 27-39.
- Cherkaev, A.V., Gibiansky, L.V., 1996. Extremal structures of multiphase heat conducting composites. *Int. J. Solids Struct.* 33(18), 2609-2623.
- Cherkaev, A., Zhang, Y., 2011. Optimal anisotropic three-phase conducting composites: Plane problem. *Int. J. Solids Struct.* 48(20), 2800-2813.
- Dacorogna, B., 2008. *Direct Methods in the Calculus of Variations*. Second edition. Springer, New York.
- Gibiansky, L.V., Sigmund, O., 2000. Multiphase composites with extremal bulk modulus. *J. Mech. Phys. Solids* 48(3), 461-498.
- Hashin, Z., Shtrikman, S., 1963. A variational approach to the theory of the elastic behaviour of multiphase materials. *J. Mech. Phys. Solids* 11(2), 127-140.

- Lurie, K.A., 1993. Applied Optimal Control Theory of Distributed Systems. Plenum Press, New York.
- Lurie, K.A., Cherkaev, A.V., 1982. Exact estimates of conductivity of composites formed by two isotropically conducting media taken in prescribed proportion. Report 783, Acad. Sci. U.S.S.R., A.F. Ioffe Physical Technical Institute, Leningrad, U.S.S.R. (in Russian). English translation in: Proc. Roy. Soc. Edinb. A 99 (1-2), pp. 71-87 (1984).
- Lurie, K.A., Cherkaev, A.V., 1985. Optimization of properties of multicomponent isotropic components. J. Optimiz. Theory App. 46(4), 571-580.
- Lurie, K.A., Cherkaev, A.V., 1986. Effective characteristics of composite materials and the optimal design of structural elements. Uspekhi Mekhaniki 9(2), 3-81 (in Russian). English translation in: Cherkaev, A. and Kohn, R. (Eds.), Topics in the Mathematical Modelling of Composite Materials, Birkhäuser, Boston, pp. 175-271 (1997).
- Milton, G.W., 1981. Bounds on the electromagnetic, elastic, and other properties of two-component composites. Phys. Rev. Lett. 46(8), 542-545.
- Milton, G.W., 1981. Concerning bounds on the transport and mechanical properties of multicomponent composite materials. Appl. Phys. A Solids and Surfaces 26(2), 125-130.
- Milton, G.W., 2002. The Theory of Composites. University Press, Cambridge.
- Milton, G.W., Kohn, R.V., 1988. Variational bounds on the effective moduli of anisotropic composites. J. Mech. Phys. Solids 36(6), 597-629.
- Nesi, V., 1995. Bounds on the effective conductivity of two-dimensional composites made of $n \geq 3$ isotropic phases in prescribed volume fraction: the weighted translation method. Proc. Roy. Soc. Edinb. A 125(6), 1219-1239.
- Tartar, L., 1985. Estimation fines des coefficients homogénéisés. In: Kree, P. (Ed.), Ennio De Giorgi's Colloquium, Research Notes in Mathematics 125, Pitman Press, London, pp. 168-187.
- Tartar, L., 2000. An Introduction to the Homogenization Method in Optimal Design. In: Cellina, A., Ornelas, A. (Eds.). Optimal Shape Design. Lecture Notes in Mathematics 1740, Springer, Berlin, pp. 47-156.